


Phase Equilibria and Thermochemistry of Selected Sulfide Systems in the Pyrometallurgy of Ni and Cu

Fiseha Tesfaye, Pekka Taskinen

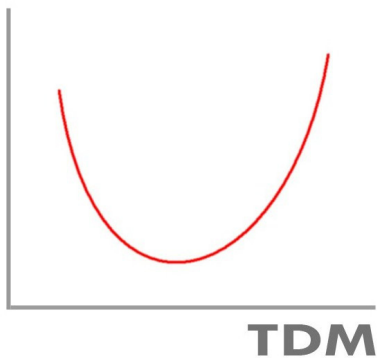

Phase Equilibria and Thermochemistry of Selected Sulfide Systems in the Pyrometallurgy of Ni and Cu

Fiseha Tesfaye, Pekka Taskinen

Aalto University publication series
SCIENCE + TECHNOLOGY 5/2012

© Fiseha Tesfaye, Pekka Taskinen

24.02.2012

ISBN 978-952-60-4531-3 (printed)

ISBN 978-952-60-4532-0 (pdf)

ISSN-L 1799-4896

ISSN 1799-4896 (printed)

ISSN 1799-490X (pdf)

Unigrafia Oy
Helsinki 2012

Finland

Publication orders (printed book):

pekka.taskinen@aalto.fi,

http://materials.tkk.fi/fi/tutkimusryhmat/metallurgiset_prosessit/

Outotec (Finland) Oy, Boliden Harjavalta Oy, Boliden Kokkola Oy,
Norilsk Nickel Finland Oy and Tekes (the Finnish Funding Agency
for Technology and Innovation)

Author

Author(s): Fiseha Tesfaye & Pekka Taskinen

Name of the publication

Phase Equilibria and Thermochemistry of Selected Sulfide Systems in the Pyrometallurgy of Ni and Cu

Publisher School of Chemical Technology**Unit** Department of Materials Science and Engineering**Series** Aalto University publication series SCIENCE + TECHNOLOGY 5/2012**Field of research** Metallurgy**Abstract**

A review of phase equilibria and thermodynamic data of Ni-(As, Se)-S and Cu-(As, Bi, Pb, Sb, Se, Te, Nb, Zn, Mo)-S systems was done. Particular emphases were given to the compilation and refine of the standard Gibbs energies of formations of equilibrium phases, which are of interest in the pyrometallurgical processes of copper and nickel production. Phase stabilities, phase relations and solubility limits of some equilibrium phases in the Ni-(As, Se)-S and Cu-Mo-Bi-Nb-S systems were also compiled and reviewed, based on the available literature.

This work also reviews, updates, and extends the earlier reports. The Gibbs energies of formations and reactions are mostly presented as linear equations, in each temperature ranges of phase stabilities. List of thermal stabilities of some pure sulfides and sulfosalts were also reviewed and compiled (Appendix).

Keywords Cu, Ni, sulfide, sulfosalt, thermodynamics, phase equilibrium**ISBN (printed)** 978-952-60-4531-3**ISBN (pdf)** 978-952-60-4532-0**ISSN-L** 1799-4896**ISSN (printed)** 1799-4896**ISSN (pdf)** 1799-490X**Location of publisher** Espoo**Location of printing** Helsinki**Year** 2012**Pages** 39

Table of Contents

| | |
|---|----|
| Table of Contents | 1 |
| Symbols, Abbreviations, Units | 2 |
| 1 Introduction | 3 |
| 1.1 Gibbs Energies of Formations of the Sulfosalts | 3 |
| 2 Phase Equilibria | 5 |
| 2.1 The Ni-As-Se-S System | 5 |
| 2.1.1 Ni-Se | 5 |
| 2.1.2 As-S-Se | 6 |
| 2.2 The Cu-Mo-Bi-Nb-S System | 10 |
| 2.2.1 Cu-Mo-Bi-S System | 11 |
| 2.2.2 Cu-Nb-S System | 14 |
| 3 Thermochemical Data | 16 |
| 4 Discussion | 25 |
| 5 Summary and Conclusions | 27 |
| References | 28 |
| Appendix | 37 |

Symbols, Abbreviations, Units

| | |
|------------------------|--|
| G, (g), V | gas phase, vapor |
| L, (l) | liquid |
| s | solid |
| (s, l) | solid or liquid based on the temperature condition |
| T | temperature [K] |
| T _m | melting temperature [K] |
| T _{max} | maximum temperature of stability [K] |
| T _{liq} | liquidus temperature [K] |
| T _{sol} | solidus temperature [K] |
| x _i | composition of component i |
| ss | solid solution |
| ΔG_f° | standard Gibbs energy of formation [J/mol] |
| ΔG_r | standard Gibbs energy of reaction [J/mol] |
| ΔG_{mix} | Gibbs energy of mixing [J/mol] |
| ΔH_{mix}° | heat of mixing [J/mol] |
| ΔS_{mix}° | entropy of mixing [J/mol.K] |
| R | 8.314472(15) [J/mol.K] |
| T(K) – T(°C) | 273.15 |
| J/cal. | 4.1868 |

1 Introduction

Due to increasing association of impurities in the copper and nickel ore minerals and concentrates, the production of high grade Cu and Ni by the conventional pyrometallurgical processes is compromised. Thus, smelters are in need to modify their operating flow sheets and strategies for processing more complex feed materials economically, while meeting the strict environmental regulations. To make the appropriate modifications, a thorough evaluation of the thermochemistry and thermal stabilities of phases and phase assemblages existing in these complex ore minerals is essential.

In the previous reports [3, 4, 5, 6], the phase equilibria and thermodynamic properties of the pure binary sulfides in the (Fe, Ni, Cu, Zn)-S systems and their ternaries as well as the (Ni, Cu)-(As, Sb)-S, Cu-Bi-S and Zn-As-Cu-Pb-S systems were discussed. In this report, phase relations in the Ni-As-Se-S system, for which the phase equilibria studies were not included in the previous reports were reviewed. Experimental data and estimates of standard Gibbs energies of formations and reactions of equilibrium phases in the systems which are studied in this and earlier reports are refined and summarized in chapter 3. Thermal stabilities of some pure sulfides and sulfosalts (including the previous studies) are also compiled (see Appendix).

The main purpose of this study was to selectively review and compile thermodynamic properties of equilibrium phases and their assemblages that are of interest in the pyrometallurgical processes of copper and nickel production. The intention was to contribute to the evaluation of the behavior of impurities in copper and nickel minerals and concentrates processing operations.

1.1 Gibbs Energies of Formations of the Sulfosalts

Most sulfosalts may be regarded as intermediate phases on the joins between simple sulfide components. For instance, sulfosalts in the Pb-Bi-S and Ag-Bi-S systems lie on the joins $\text{PbS-Bi}_2\text{S}_3$ and $\text{Ag}_2\text{S-Bi}_2\text{S}_3$, respectively.

Therefore, the chemical compositions of the sulfosalts are, in general, stoichiometric, having formula consistent with normal valences of the elements. Furthermore, many of the structures are similar to those of the component simple sulfides such as galena-like and stibnite-like layers in lead sulfantimonides [7].

The sulfosalts constitute a large and complex group of ore minerals. Although the sulfosalts rarely form massive ore bodies, they have proven sources of valuable metals. They are commonly encountered with rich sulfide ores of Ag, Cu, Pb, Fe and Ni; and they are widely distributed in poor mineral rocks [8]. However, thermochemical data for the sulfosalt minerals are available only for few systems and experimentally determined thermodynamic properties are limited.

By combining new and old data from the literature regarding the thermodynamic functions of the sulfosalt minerals, with a few simple assumptions, may permit calculation of new thermochemical data for a number of sulfosalt minerals that are well characterized. As these data are working approximations, they must be refined for tasks that require greater accuracy.

2 Phase Equilibria

Phase relations in (Ni, Cu, Zn)-S, (Ni, Cu)-(As, Sb)-S, Cu-Bi-S and Zn-As-Cu-Pb-S sulfide systems were discussed in the previous reports [3, 4, 5, 6]. In this study, phase equilibria in the Ni-As-Se-S and Cu-Mo-Nb-Bi-S systems, which were not included in the previous reports, will be selectively discussed. Thermal stabilities of some pure sulfides and sulfosalts (including the previous studies) are also compiled (Appendix). Gibbs energies of formation of the equilibrium phases for which experimental data or estimates are available in the broader system (including phase equilibria studied in the previous works) were reviewed and compiled in chapter 3 (Table 4).

2.1 The Ni-As-Se-S System

Minerals and compounds in the Ni-As-S system are maucherite ($\text{Ni}_{11}\text{As}_8$), niccolite (Ni_{1+x}As), NiAs_2 -polymorphs (rammelsbergite and paramrammelsbergite), Ni_5As_2 , vaesite (NiS_2), polydymite (Ni_3S_4), millerite (Ni_{1-x}S), heazlewoodite (Ni_3S_4), $\text{Ni}_{3+x}\text{S}_2$, Ni_7S_6 , orpiment (As_2S_3), realgar (AsS) and Gersdorffite with a wide compositional range (NiAsS). Details about their phase relations were reviewed in [4, 5] and their thermodynamic properties are summarized in chapter 3 and Appendix. In this section, phase equilibria of the systems As-Se-S and Ni-Se will be discussed.

2.1.1 Ni-Se

This system is comprised of five intermediate binary phases, as listed in Table 1. The melting temperature of Ni (1455.15 °C) and Se (220.85 °C) was taken from [9]. An assessed phase diagram of the Ni-Se system by Lee & Nash [10] is shown in Figure 1. In a study based on measurements of lattice parameter, Kuznecov [11] reported the solubility of Se in (Ni) at 620 °C to be less than 0.1 at. % Se. A metastable phase $\alpha'\text{Ni}_2\text{Se}_3$ has also been reported by Kuznecov [11] as a polymorphic transitions $\alpha'\text{Ni}_2\text{Se}_3 \leftrightarrow \beta\text{Ni}_2\text{Se}_3$ and $\alpha\text{Ni}_2\text{Se}_3 \leftrightarrow \alpha'\text{Ni}_2\text{Se}_3$ at 620 °C and 590 °C, respectively.

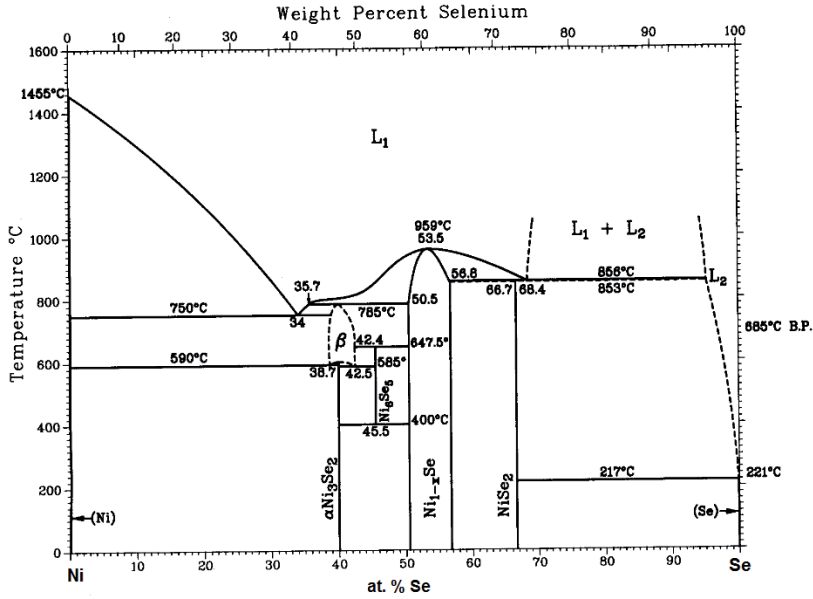


Figure 1. The Ni-Se phase diagram [12].

Table 1. Phase transformation reactions in the Ni-Se system [10, 9]. Composition of Se is written according to the arrangement of phases in the reactions.

| Reaction | at. % Se | T(°C) | Reaction type | Ref. |
|--|--------------------|--------|---------------|------|
| Ni ↔ L | 0 | 1455.2 | Melting | [9] |
| $\beta\text{Ni}_{3\pm x}\text{Se}_2 \leftrightarrow \alpha\text{Ni}_3\text{Se}_2$ | 40 | 600 | Polymorphic | [10] |
| $\text{Ni}_{1-x}\text{Se} \leftrightarrow \text{L}$ | 53.5 | 959 | Congruent | [10] |
| (Ni) + $\beta \leftrightarrow \text{L1}$ | 0 39.2 34 | 750 | Eutectic | [10] |
| (Se) + $\text{NiSe}_2 \leftrightarrow \text{L2}$ | 100 66.7 100 | 217 | Eutectic | [10] |
| $\text{Ni}_6\text{Se}_5 \leftrightarrow \alpha\text{Ni}_3\text{Se}_2 + \alpha\text{Ni}_{1-x}\text{Se}$ | 45.5 40 50.5 | 400 | Eutectoid | [10] |
| $\beta\text{Ni}_{3\pm x}\text{Se}_2 \leftrightarrow (\text{Ni}) + \alpha\text{Ni}_3\text{Se}_2$ | 38.7 0 40 | 590 | Eutectoid | [10] |
| $\beta\text{Ni}_{3\pm x}\text{Se}_2 \leftrightarrow \alpha\text{Ni}_3\text{Se}_2 + \text{Ni}_6\text{Se}_5$ | 42.5 40 45.5 | 585 | Eutectoid | [10] |
| $\text{L1} + \text{Ni}_{1-x}\text{Se} \leftrightarrow \beta\text{Ni}_3\text{Se}_2$ | 35.7 50.5 40 | 785 | Peritectic | [10] |
| $\text{Ni}_{1-x}\text{Se} + \text{L2} \leftrightarrow \text{NiSe}_2$ | 56.8 95.1 66.7 | ~ 853 | Peritectic | [10] |
| $\beta\text{Ni}_{3\pm x}\text{Se}_2 + \text{Ni}_{1-x}\text{Se} \leftrightarrow \alpha\text{Ni}_6\text{Se}_5$ | 42.4 50.5 45.5 | 647.5 | Peritectoid | [10] |
| $\text{L1} \leftrightarrow \text{Ni}_{1-x}\text{Se} + \text{L2}$ | 68.4 56.8 95.1 | 856 | Monotectic | [10] |
| Se ↔ L | 100 | 220.85 | Melting | [9] |

2.1.2 As-S-Se

Partial phase diagram of the As-Se system, in the composition range 40 – 100 wt. % Se, is shown in Figure 2. An optimized condensed phase diagram

of the Se-As system along with selected experimental points is shown in Figure 3. Amorphous Se undergoes a glassy transition at about 30.25 °C [13]. Mass-spectrometric studies by Drowart et al. [14] revealed the presence of Se₁ to Se₈ species in the vapor. According to their results Se₂, Se₅, Se₆, and Se₇ are the major species depending on the temperature.

Dembovskii and Luzhnaya [15] studied the Se-As system by DTA for compositions up to about 70 mol. % As. Consequently, they found two congruently melting compounds, As₂Se₃ and AsSe. According to Blachnik et al. [16], AsSe melts peritectically at 264 °C, rather than congruently at 295 °C [15], and the polymorphic transition temperature of As₄Se₃ is 174 °C. Myers and Felty [17] employed static quench techniques to study the phase diagram for compositions up to 60 mol. % As. No details of the experiments and no experimental points were given, however, from their phase diagram the invariant points are derived and collected in Table 3. A result of X-ray analysis indicated that AsSe crystallizes in the realgar structure, which corresponds to the formula As₄Se₄ [13].

By using the Fluorine-combustion calorimetry method, O'Hare et al. [18] determined the enthalpy of the transition from vitreous to the crystalline forms of As₂Se₃ to be $-(28.0 \pm 3.9)$ kJ/mol., at 298.15 K, and $\Delta_f H_m^\circ$ (As₂Se₃, crystalline) = $-(86.1 \pm 4.1)$ kJ/mol. and $\Delta_f H_m^\circ$ (As₂Se₃, vitreous) = $-(58.1 \pm 4.2)$ kJ/mol., both at standard conditions. According to O'Hare et al. [18] the melting temperature of As₂Se₃ is about 359.85 °C. Enthalpies of high-temperature decomposition of As₂Se₃ along with derived molar heats of formation, at room temperature are shown in Table 2.

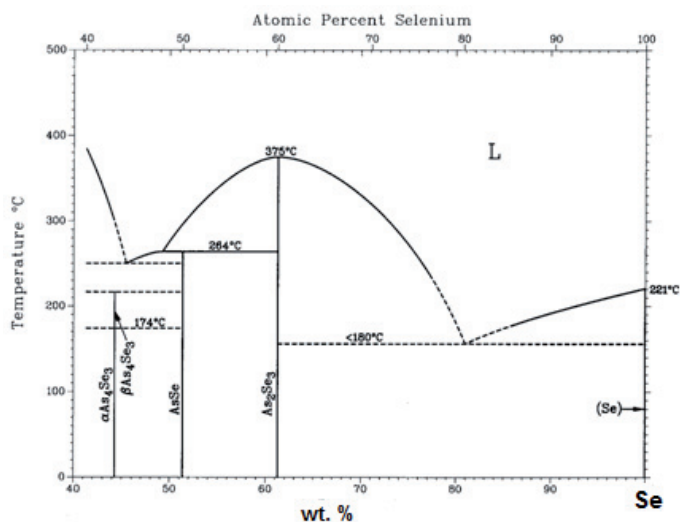


Figure 2. The As-Se phase diagram [12].

Table 2. Enthalpies of high-temperature decomposition of As_2Se_3 and derived $\Delta_f H_m^o$ values at 298.15 K [18, 19]. For the derivation of $\Delta_f H_m^o (\text{As}_2\text{Se}_3(\text{s}), \text{kJ/mol})$, the following auxiliary values were used: $\Delta_f H_m^o (\text{As}_4(\text{g}), \frac{\text{kJ}}{\text{mol}}) = 158.2 \pm 2.5$ and $\Delta_f H_m^o (\text{Se}_2(\text{g}), \frac{\text{kJ}}{\text{mol}}) = 144.1 \pm 0.6$.

| Reaction | $\Delta_r H_m^o (\text{kJ/mol})$ [19] | $\Delta_f H_m^o (\text{As}_2\text{Se}_3(\text{s}), \text{kJ/mol})$ [18] |
|---|--|--|
| $\text{As}_2\text{Se}_3(\text{vit}) = \frac{1}{2}\text{As}_4\text{Se}_3(\text{g}) + \frac{3}{4}\text{Se}_2(\text{g})$ | 222.8 ± 8.0 | -59 ± 9 |
| $\frac{1}{2}\text{As}_4(\text{g}) + \frac{3}{4}\text{Se}_2(\text{g}) = \frac{1}{2}\text{As}_4\text{Se}_3(\text{g})$ | -131.3 ± 3.0 | - |
| $\text{As}_2\text{Se}_3(\text{vit}) = \frac{1}{2}\text{As}_4\text{Se}_4(\text{g}) + \frac{1}{2}\text{Se}_2(\text{g})$ | 177.8 ± 7.0 | -49 ± 8 |
| $\frac{1}{2}\text{As}_4(\text{g}) + \text{Se}_2(\text{g}) = \frac{1}{2}\text{As}_4\text{Se}_4(\text{g})$ | -166.5 ± 3.0 | - |
| $\text{As}_2\text{Se}_3(\text{s}) = \frac{1}{2}\text{As}_4\text{Se}_3(\text{g}) + \frac{3}{4}\text{Se}_2(\text{g})$ | 259.4 ± 8.0 | -95 ± 9 |
| $\text{As}_2\text{Se}_3(\text{s}) = \frac{1}{2}\text{As}_4\text{Se}_4(\text{g}) + \frac{1}{2}\text{Se}_2(\text{g})$ | 219.7 ± 7.0 | -91 ± 8 |

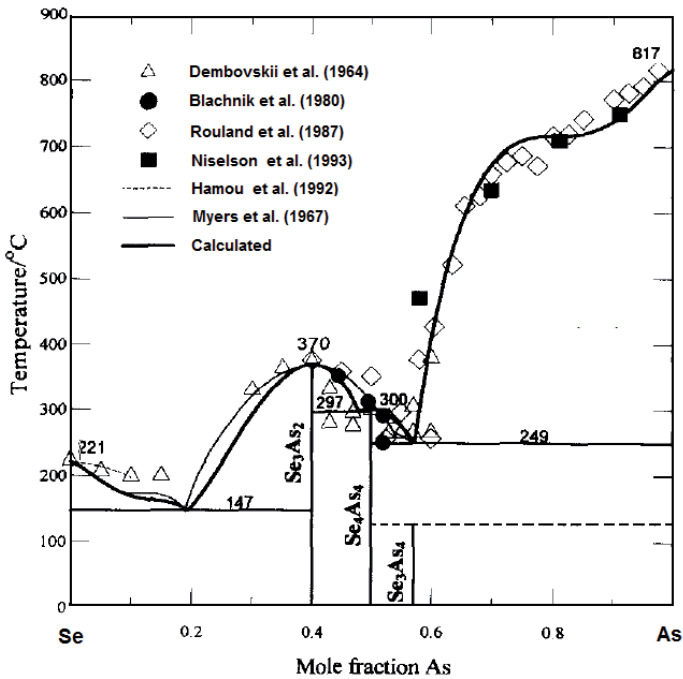


Figure 3. A condensed phase diagram of the System As-Se [13].

Phase diagram of the S-Se system is shown in Figure 4. Solid sulfur exists in two allotropic forms α -S, stable up to 95.5 °C, and β -S, stable from 95.5 °C to its melting point (115.22 °C) [20]. Se exists in one crystal structure form up to its melting point at 221 °C [9, 20]. The phase diagram is essentially determined by Ringer [21] by thermal and dilatometric methods. Sharma and Chang [20, 22] have made modifications with regard to the

then accepted melting points of S and Se. In addition to the primary solid solutions (α S), (β S) and Se, there exists an intermediate phase, γ , with a wide composition range (48.7 – 83 at. % Se) [22]. The invariant points in this system are also collected in Table 3.

According to Boudreau and Haendler [23] there exists several metastable phases in the S-Se system, mostly based on the known structures of S and Se. Geller and Lind [24] reported a trigonal phase $S_{0.555}Se_{0.455}$ to form when equiatomic compositions are mixed and subjected to a pressure of 20 Kbar at 280 °C.

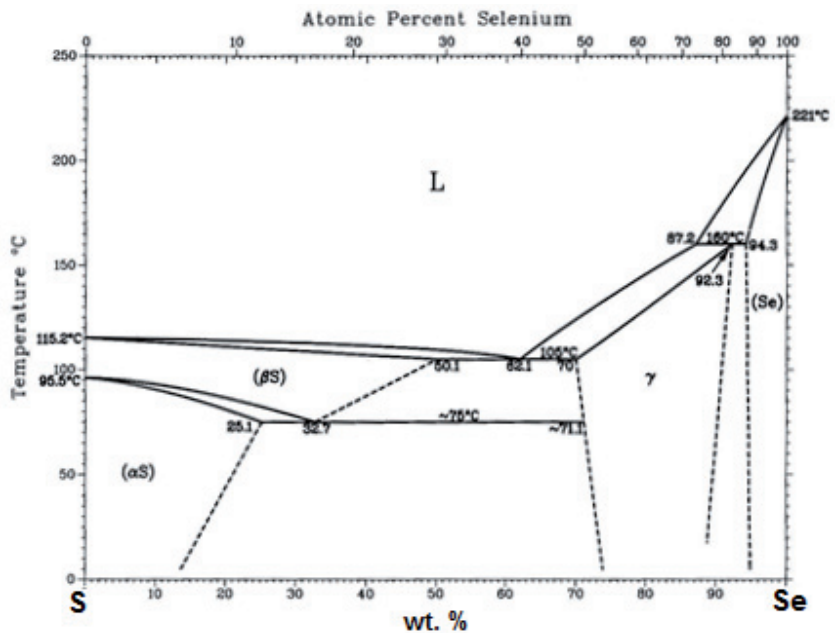


Figure 4. The S – Se phase diagram [20].

Phase relations in the $As_2S_3 - As_2Se_3$ system have been studied by the DTA method, using a Kurnakov pyrometer with Pt-PtRh thermocouples, by Zhukov et al. [25]. They studied end-members of six intermediate compositions (10, 25, 35, 55, 75, 95 mol% As_2Se_3). Their results showed that the system forms a continuous series of solid solutions (ss), as shown in Figure 5, and the glass transition temperature for the whole system is constant and occurs at 180 ± 5 °C.

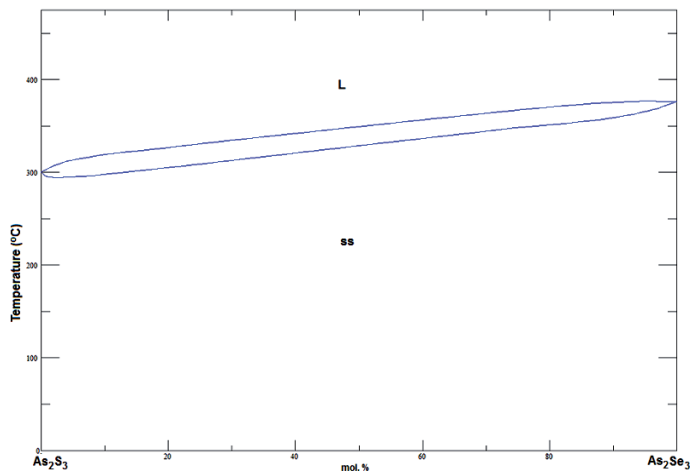


Figure 5. Phase relations in the $\text{As}_2\text{S}_3 - \text{As}_2\text{Se}_3$ system [26].

Table 3. Phase change reactions in the As-Se and S-Se systems [9, 22, 27]. Composition of Se is written according to the arrangement of phases in the reactions. The composition range for γ is 48.7 – 83 at. % Se.

| Reaction | at. % Se | T(°C) | Reaction type | Ref. |
|---|-----------------|--------|-------------------|------|
| $\text{L} \leftrightarrow \beta\text{S}$ | 0 | 115.22 | Melting | [22] |
| $\beta\text{S} \leftrightarrow \alpha\text{S}$ | 0 | 95.5 | Allotropic | [22] |
| $(\beta\text{S}) \leftrightarrow (\alpha\text{S}) + \gamma$ | 16.5 12 ~50 | 75 | Eutectoid | [22] |
| $\text{L} \leftrightarrow (\beta\text{S}) + \gamma$ | 40 29 48.7 | 105 | Eutectic | [22] |
| $\text{L} + (\text{Se}) \leftrightarrow \gamma$ | 73.5 87 83 | 160 | Peritectic | [22] |
| $\text{Se} \leftrightarrow \text{L}$ | 100 | 220.85 | Melting | [9] |
| $\text{L} \leftrightarrow \text{Se} + \text{As}_2\text{Se}_3$ | - | 146 | Eutectic | [27] |
| $\text{As}_2\text{Se}_3 \leftrightarrow \text{L}$ | 60 - | 370 | Congruent melting | [27] |
| $\text{L} + \text{As}_2\text{S}_3 \leftrightarrow \text{As}_4\text{Se}_4$ | - | 265 | Peritectic | [27] |
| $\text{L} \leftrightarrow \text{As}_4\text{Se}_4 + \text{As}$ | - | 250 | Eutectic | [27] |

2.2 The Cu-Mo-Bi-Nb-S System

Phase relations in the Cu-Bi-S system have been reviewed in the previous report [5]. There are no intermediate phases in the metal-metal systems; Cu-Mo [28], Cu-Bi [12], Mo-Nb [12], Mo-Bi [12], Nb-Bi [12] and Cu-Nb

[30], and in this section phase relations in the Cu-Mo-Bi-S and Cu-Nb-S systems will be discussed. The Gibbs energies of formations and sulfidation reactions of some the stable phases are summarized in chapter 3.

2.2.1 Cu-Mo-Bi-S System

A review of phase relations in this system is done through two major systems Mo-Bi-S and Cu-Mo-S.

2.2.1.1 Mo-Bi-S

Mo melts at high temperature of 2622.85 °C [9]; consequently, the lowest melting point of its sulfides is above 1450 °C. Phase diagram of the Mo-S system obtained by thermodynamic modeling is shown in Figure 6. According to Brewer & Lamoreaux [29], the system is characterized by two stable intermediate phases Mo_2S_3 (mP10) and MoS_2 (hP6). Sulfur rich amorphous phase, MoS_3 , was reported to have been prepared by decomposition of sulfomolybdates. The amorphous phase transforms to $\text{Mo}_{0.83}\text{S}_2$ up on heating above 200 °C [30].

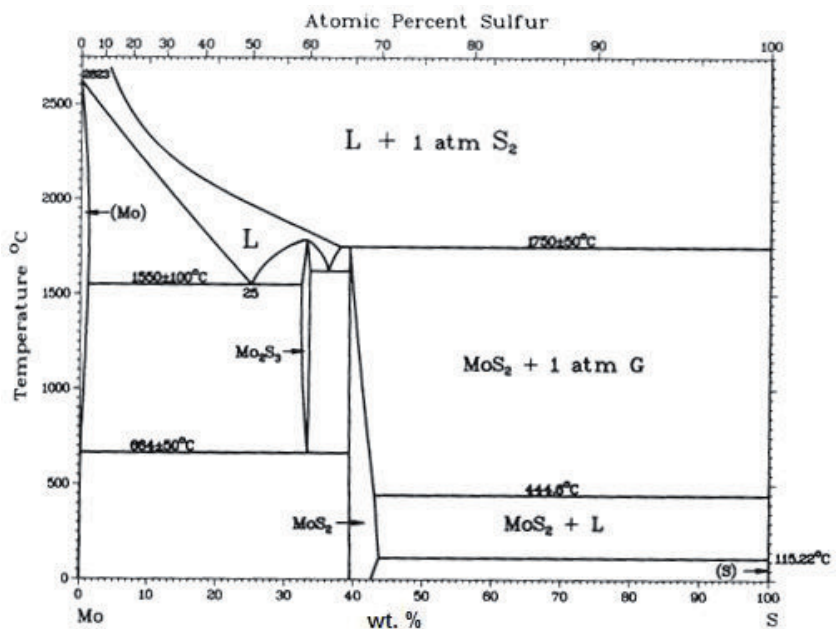


Figure 6. The Mo-S phase diagram [12].

While studying the Sn, W and Mo type of ores, Stempok [31] reported native Bi, Bi_2S_3 and MoS_2 to occur in association with ore minerals such as cassiterite (SnO_2), wolframite (WO_4), arsenopyrite (FeAsS), chalcopyrite

(CuFeS_{2-x}) and pyrite (FeS_2), where quartz, micas, topaz, tourmaline, and fluorite are the main gangue minerals.

Phase relations in the Mo-Bi-S system, below the crystallization temperature of Bi_2S_3 , 760 °C [31], are shown in Figure 7 and Figure 8. There exists a tie line between Bi_2S_3 and MoS_2 . The Bi-S liquid field decreases in extent with decreasing temperature. At about 610 °C the Mo_2S_3 phase becomes unstable, and below this temperature MoS_2 coexists with metallic Mo. The phase relations slightly below the 610 °C are shown in Figure 7. Below the melting point of Bi (271.4 °C [9]) close to the corner of pure Bi, eutectic exists at about 270 °C [12]. According to Stemprok [31], experiments in which small amounts of MoS_2 were added to Bi-S mixtures of a composition near the binary eutectic did not result in any melt formation below 267 °C, which indicates that a ternary eutectic does not exist.

The solubility of MoS_2 and Mo_2S_3 in liquid Bi investigated by Stemprok [31], at temperatures between 400 - 1200 °C, have been shown to be considerably less than 1 wt. %. Similarly, the solubility of MoS_2 in Bi_2S_3 (s), at 700 °C, and in Bi_2S_3 (l), at 920 °C, are less than 1 wt. %. Likewise, the solubility of Bi and Bi_2S_3 in MoS_2 at 700 °C are less than 1 wt. %. The maximum Bi content of MoS_2 is 0.24 wt. % [31] and the Mo content of native Bi and Bi_2S_3 was reported to be about 0.00002 wt. % [32].

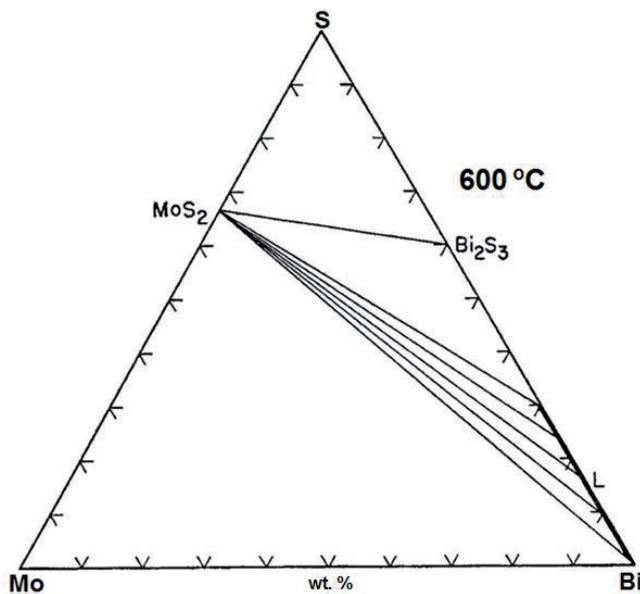


Figure 7. Phase relations in the Mo-Bi-S system at 600 °C. The solubility of molybdenite (MoS_2) in liquid L is much less than 1 wt. % [31].


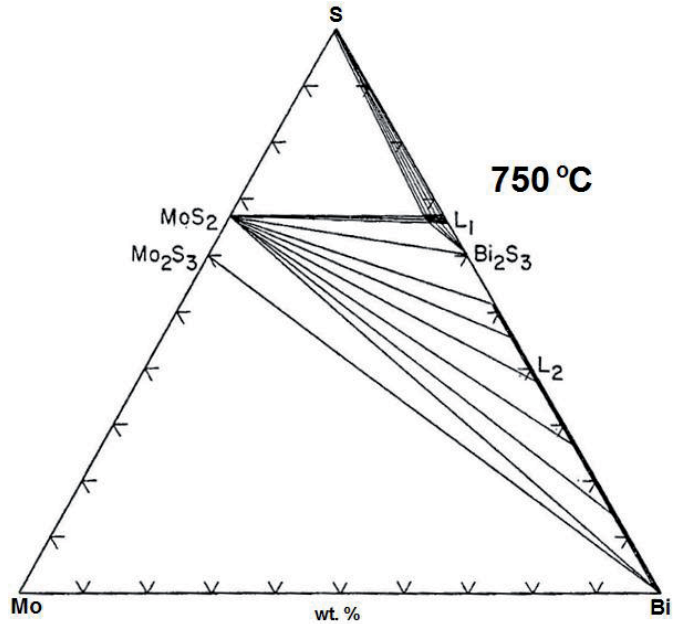


Figure 8. Phase relations in the Mo-Bi-S system at 750 °C. The solubility of molybdenite (MoS_2) in liquid L_1 was slightly exaggerated to reveal the phase relations. Tie line between MoS_2 and Bi_2S_3 prohibits equilibrium coexistence of Mo_2S_3 and Bi_2S_3 [31].

2.2.1.2 Cu-Mo-S

Phase relations in the binary Mo-S system were discussed in section 2.2.1.1. The ternary phase relations in the Cu-Mo-S system have been investigated by Grover [33] and Grover & Moh [34]. According to their studies, at about 1000 °C a miscibility gap between the sulfur-rich and sulfide-rich melts exists close to the Cu-S binary.

According to Chang et al. [30], the Cu-Mo-S system comprises a single ternary phase; $\sim\text{CuMo}_2\text{S}_3$, with small homogeneity range and thermal stability range between 594 and > 1000 °C, which was characterized by Grover [33]. Below 813 °C, a sulfide-rich liquid of ~1 wt. % Mo cease to exist and Cu_{2-x}S phase coexists with S-rich liquid (L_1) as shown in Figure 9. As temperature decreases, the homogeneity range of $\sim\text{CuMo}_2\text{S}_3$ narrows and at 685 °C the following equilibrium can be expressed as Reaction (I):



Below about 594 °C, the ternary phase does not any more exist [30].

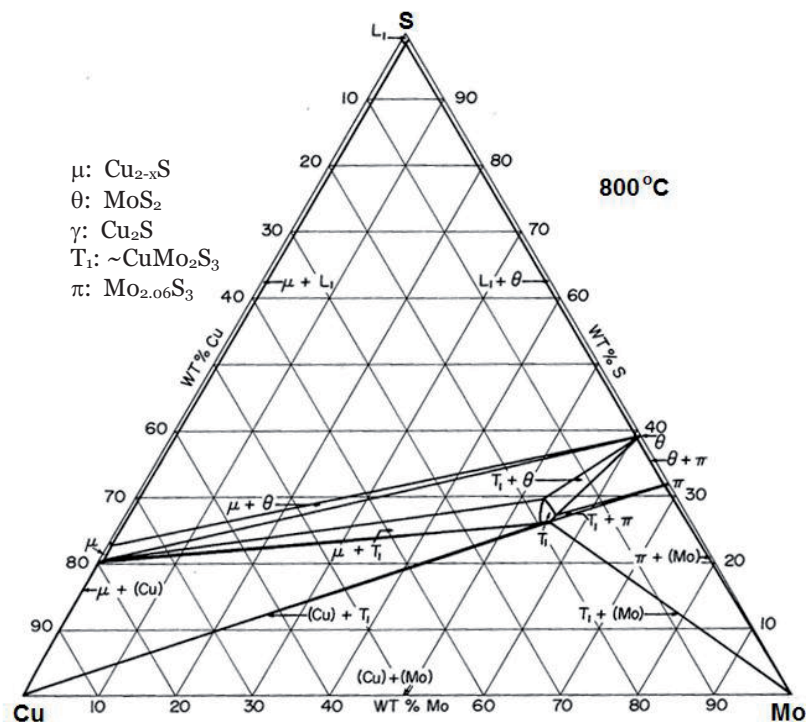


Figure 9. Phase relations in the Cu-Mo-S system at 800 °C [30].

2.2.2 Cu-Nb-S System

A large number of Nb-sulfides are reported in the literature. Biltz and Kocherz [35] noted the presence of $\text{NbS}_{0.5-1.0}$, Nb_2S_3 , and NbS_2 . Jellinek [36, 37] disputes these early results and instead reports the 'stable' phases NbS_3 , NbS_2 (rhomb.), NbS_2 (hex.), $\text{Nb}_{1+x}\text{S}_2$ (rhomb.), and $\text{Nb}_{1+x}\text{S}_2$ (hex.). Hodouin [38] notes the formation of NbS , Nb_3S_4 , $\text{Nb}_{1+x}\text{S}_2$ (hex.), $\text{Nb}_{1+x}\text{S}_2$ (rhomb.), and NbS_2 at 1273 K. Hartman and Wagner [39] reported the formation of Nb_4S_7 . Presently, there are discrepancies in the phase limits reported by various authors in addition to the particular compounds present at equilibrium.

The Nb-S phase diagram redrawn by Massalski [12] from [40] is shown in Figure 10. According to [9] Nb melts at 2476.85 °C. Selected stable intermediate phases reported by different researchers in the system are $\text{Nb}_{14}\text{S}_{15}$ [41], Nb_{21}S_8 [40], Nb_{10}S_9 [40], NbS [42], Nb_3S_4 [35, 40], NbS_2 [35, 40] and NbS_3 [40]. NbS exists in two modifications (hexagonal) α - NbS and

(orthorhombic) β -NbS. The α - to β -NbS transition is reported to take place at 780 °C on heating and at 740 °C on cooling [42]. NbS₂ also occurs in two forms (rhombohedral) α -NbS₂ (stable below 850 °C [40]) and (hexagonal) β -NbS₂ (stable in the temperature range ~850 – 1050 °C [37]). Except Chen's et al. [41] report for Nb₁₄S₅ to melt at slightly above 1500 °C, the melting points of the intermediate phases are not available.

No intermediate phases appear in the Cu-Nb system [30]. In the broader Cu-Nb-S system, there are two ternary phases; Cu₃NbS₄ and Cu_{0.7}NbS₂, which are characterized by Van Arkel & Crevecoeur [43].

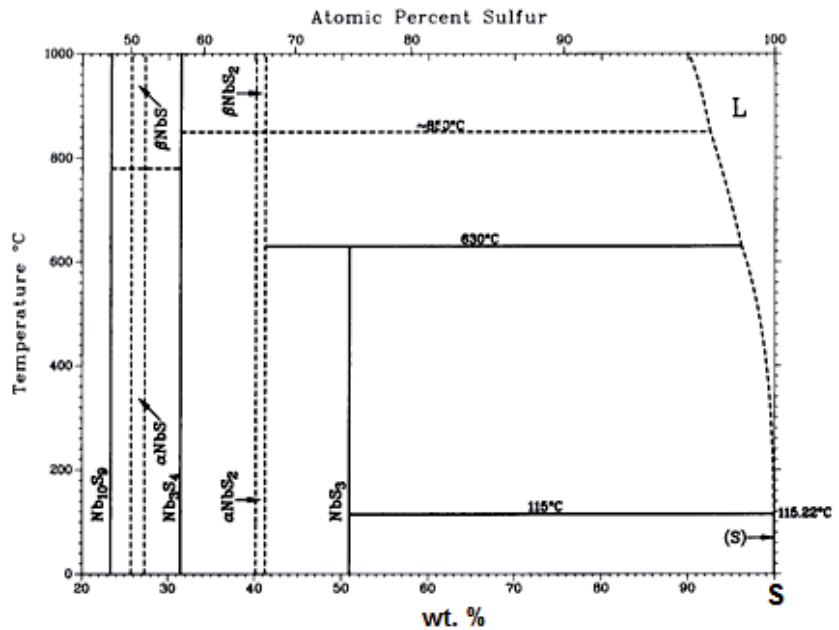


Figure 10. The Nb-S phase diagram [12]. Melting points of the intermediate phases are largely unknown.

3 Thermochemical Data

Earlier, Craig & Barton [7], Craig & Lee [8] and Lynch [44] compiled preliminary estimates and experimental data on the thermodynamic properties of sulfides, arsenides, sulfosalts, some of them are also included in Table 4. The former authors have also estimated the Gibbs energies for sulfidation reactions of sulfides and sulfosalts. The thermochemical data could be used in the prediction of the general behavior of sulfosalts and the stabilities in dry systems, as well as in improving procedures for extraction and refining of valuable metals from sulfide ores [7]. However, the data may not be sufficiently precise to predict the detailed structures of the complex phase diagrams.

The basic elemental and sulfide data on which the sulfosalt calculations are based have been documented and the assumptions are straight forward. In this study, we present a selective compilation of the Gibbs energies of formation data for some phases and sulfidation reactions which are of interest in the pyrometallurgy of Cu and Ni.

Equations for some of the Gibbs energies of formations and reactions were obtained by linear fitting and extrapolation of experimental data, within the temperature ranges of phase stabilities.

Table 4. Compilation of experimentally determined and estimated thermodynamic data of stable phases and phase assemblages in the Ni-(As, Se)-S and Cu-(As, Bi, Pb, Sb, Se, Te, Nb, Zn, Mo)-S systems. Standard states: S₂(g), As(s), Sb(s), Pb(s), Cu(s), Ni(s), Mo(s), Se(s,l), and Zn(s). The Gibbs energies of formation of all reactions are calculated or determined as written.

| Reaction | $\Delta G_{T(K)}$ (J/mol) | T(K) | Ref. | Remarks |
|--|--|------------|----------|-----------------------------------|
| Ni-As-Se-S | | | | |
| As(s) = As(l) | 23645 - 21.7·T | 1098 | [45] | experimental |
| As(s) = As(g) | 287997 - 157.1·T + 5.901·T·logT + 2.626·10 ⁻³ ·T ² | 298- 1600 | [47] | |
| 2As(s) = As ₂ (g) | 193580 - 244.3·T + 24.88·T·logT + 4.670·10 ⁻³ ·T ² | 298- 1600 | | |
| 3As(s) = As ₃ (g) | 219490 - 272.8T + 22.64·T·logT + 7.027·(10 ⁻³)·T ² | 298- 1600 | | |
| 4As(s) = As ₄ (g) | 160700 - 279.8·T + 31.07·T·logT + 9.317·10 ⁻³ ·T ² | 298 - 1600 | | |
| 2As(s) + $\frac{3}{2}$ S ₂ (g) = As ₂ S ₃ (s, l) | -291.52 - 0.021·T·lnT + 0.235·(10 ⁻⁶)·T ² + 116.29·T ⁻¹ + 0.39·T | 298 - 4585 | [57] | |
| 4As(s) + 3S ₂ (g) = 2As ₂ S ₃ (l) | -491870 + 428·T | 585 - 718 | [48] | |
| 4As(s) + 2S ₂ (g) = As ₄ S ₄ (l) | -350650 + 270·T | 580 - 718 | | |
| 2As ₂ (g) + 3S ₂ (g) = As ₄ S ₄ (g) | -622920 + 461·T | 298-1000 | | |
| As ₂ (g) + S ₂ (g) = 2AsS(g) | 36410 - 22.2·T | 298 - 1000 | [49] | experimental |
| As + Ni = NiAs(s) | -73363 + 17.3·T | 298 - 800 | [45, 50] | |
| Ni(s) + $\frac{1}{4}$ As ₄ (g) + $\frac{1}{2}$ S ₂ (g) = NiAsS | -121000 + 54.7·T | 825 - 975 | [51] | |
| $\frac{1}{4}$ As ₄ (g) + NiS(s) = NiAsS | -36750 + 39.5·T | 684 - 810 | [52] | NiS contained several wt. % NiAs |
| 2As(s) + 3Se(s) = As ₂ Se ₃ (s) | -86.1 ± 4.1 - (0.99)·T | 298 - 400 | - | determined from the data of [18]. |
| 2As(s) + 3Se(s) = As ₂ Se ₃ (s) | - 92192 - 7.6308·T | 500 - 633 | - | 633 K is melting T. |
| Ni + $\frac{1}{2}$ S ₂ (g) = NiS | - 147800 + 73.3·T | 780 - 1250 | [53] | ± 2500 (J/mol) |
| 3Ni + S ₂ (g) = Ni ₃ S ₂ | - 279470 + 102.8·T | 845 - 1040 | [53] | ± 6000 (J/mol) |
| 4Ni + $\frac{3}{2}$ S ₂ (g) = Ni ₄ S ₃ | -435750 + 180.2·T | 845 - 1040 | [53] | ± 8500 (J/mol) |
| Ni + S ₂ (g) = NiS ₂ | -257010 + 170.3·T | 675 - 1070 | [54] | ± 3000 (J/mol) |

Table 4. - (Continued.)

| Cu-As-Bi-Pb-Sb-Se-Te-Nb-Zn-Mo-S | | | | |
|---|--|-------------|----------|---|
| $4\text{As}(s) + 3\text{Cu}(s) = \text{Cu}_3\text{As}(s)$ | $-108480 + 1.4 \cdot T$ | 298 - 1098 | [45, 50] | |
| $\text{As}_4(g) + 6\text{Zn}(l) = 2\text{Zn}_3\text{As}_2(s)$ | $-271960 - 346 \cdot T + 144 \cdot T \cdot \log T$ | 613 - 853 | [55] | |
| $5\text{Mo} + 2\text{As}_2(g) = \text{Mo}_5\text{As}_4$ | $-702980 + 537.4 \cdot T - 61.2 \cdot T \cdot \log T$ | 298 - 2110 | [56] | |
| $4\text{Mo}_5\text{As}_4(s) + 7\text{As}(g) = 10\text{Mo}_2\text{As}_3(s)$ | $-1913500 + 1882 \cdot T - 214.3 \cdot T \cdot \log T$ | 298 - 1520 | [56] | |
| $4\text{Mo}_2\text{As}_3(s) + \text{As}_4(g) = 8\text{MoAs}_2(s)$ | $-321600 + 595 \cdot T - 115 \cdot T \cdot \log T$ | 298 - 1340 | [56] | |
| $\text{Cu} + \text{Te} = \text{Cu}_2\text{Te}$ | $-(38100 \pm 2900) - 4.03 \cdot T$ | 298 - ? | - | determined from the data of [46] |
| $\text{Cu} + \text{Te} = \text{Cu}_4\text{Te}_3$ | $-(100000 \pm 5400) + 8.39 \cdot T$ | 298 - ? | - | determined from the data of [46] |
| $\text{Cu} + \text{Te} = \text{CuTe}$ | $-(23400 \pm 3300) - 4.36 \cdot T$ | 298 - ? | - | determined from the data of [46] |
| $\text{Nb}(s) + \text{S}(s, l) = \text{NbS}(g)$ | $425120 - 165.63 \cdot T$ | 298 - 717 | - | estimated from the data of [57] |
| $\text{Nb}(s) + 0.5 \text{S}_2(g) = \text{NbS}(g)$ | $361720 - 89.517 \cdot T$ | 298 - 2000 | - | estimated from the data of [57] |
| $\text{Nb} + \text{S}_2(g) = \text{NbS}_2$ | $-447903.864 + 159.18 \cdot T$ | 1123 - 1373 | [58] | ± 5442.84 |
| $\text{Mo} + \text{S}(s, l) = \text{MoS}_2(s)$ | $-282942 + 48.912 \cdot T$ | 298 - 717 | - | estimated from the data of [57] |
| $\text{Mo}(s) + \text{S}_2(g) = \text{MoS}_2(s)$ | $-398305 + 180.76 \cdot T$ | 298 - 2000 | - | estimated from the data of [57] |
| $2\text{Mo}(s) + 3\text{S}(s, l) = \text{Mo}_2\text{S}_3(s)$ | $-416943 + 65.565 \cdot T$ | 298 - 717 | - | estimated from the data of [57] |
| $2\text{Mo}(s) + 1.5\text{S}(g) = \text{Mo}_2\text{S}_3(s, l)$ | $-586600 + 257.6 \cdot T$ | 298 - 2140 | - | estimated from the data of [57] |
| $3\text{Cu} + \text{As} + 2\text{S}_2(g) = \text{Cu}_3\text{AsS}_4$ (Luzonite) | $-437344.8 + 235.13 \cdot T$ | 298-873 | [59] | effect of transition neglected |
| $3\text{Cu} + \text{As} + 2\text{S}_2(g) = \text{Cu}_3\text{AsS}_4$ (Enargite) | $-437344.8 + 235.13 \cdot T$ | 298-873 | [59, 60] | effect of transition neglected. |
| $\frac{2}{3}\text{Cu}_{12}\text{As}_4\text{S}_{13} + \text{S}_2(g) = \frac{8}{3}\text{Cu}_3\text{AsS}_4$ | $-174070.4 + 146.1612 \cdot T$ | 298 - 773 | [59, 60] | |
| $12\text{Cu} + 4\text{As} + \frac{13}{2}\text{S}_2(g) = \text{Cu}_{12}\text{As}_4\text{S}_{13}$ (Tennantite) | $-1488273.442 + 721.302 \cdot T$ | 298-873 | [59] | composition not well represented by formula |

Table 4. - (Continued.)

| | | | | |
|---|-----------------------------|-----------|------|--------------------------------------|
| 6Cu + 4As + $\frac{9}{2}$ S ₂ (g) = Cu ₆ As ₄ S ₉ (Sinnerite) | -989508.312 + 572.8798·T | 298-762 | [59] | |
| 9Pb + 4As + $\frac{15}{2}$ S ₂ (g) = Pb ₉ As ₄ S ₁₅ (Gratonite) | -1990446.59 + 1047.91·T | 298-523 | [61] | effect of transition neglected |
| 3PbS + $\frac{4}{3}$ As + S ₂ (g) = $\frac{1}{2}$ Pb ₉ As ₄ S ₁₅ | -192592.8 + 132.76·T | 298 - 773 | [7] | |
| 2Pb + 2As + $\frac{5}{2}$ S ₂ (g) = Pb ₂ As ₂ S ₅ (Dufrenoyesite) | -602815.46 + 360.32·T | 298-758 | [61] | |
| $\frac{1}{2}$ Pb ₉ As ₄ S ₁₅ + 4AsS + S ₂ (g) = $\frac{18}{5}$ Pb ₂ As ₂ S ₅ | -175008.2 + 115.51·T | 298 - 554 | [7] | |
| $\frac{1}{2}$ Pb ₉ As ₄ S ₁₅ + 4(S-As) _(liq.) + S ₂ (g) = $\frac{18}{5}$ Pb ₂ As ₂ S ₅ | -191755.44 + 139.8·T | 281 - 723 | [7] | |
| 3Pb + 4As + $\frac{9}{2}$ S ₂ (g) = Pb ₃ As ₄ S ₉ (Baumhauerite) | -960745 + 658.42·T | 298 - 773 | [7] | |
| 6Pb ₂ As ₂ S ₅ + 4AsS + S ₂ (g) = 4Pb ₃ As ₄ S ₉ | -175008.24 + 128.45·T | 298 - 554 | [7] | |
| 6Pb ₂ As ₂ S ₅ + 4(S-As) _(liq.) + S ₂ (g) = 4Pb ₃ As ₄ S ₉ | -191755.44 + 152.74·T | 554 - 873 | [7] | |
| Pb + 2As + 2S ₂ (g) = PbAs ₂ S ₄ (Sartorite) | -445852.33 + 299.27·T | 298 - ? | [7] | formula uncertain |
| 13Pb + 18As + 20S ₂ (g) = Pb ₁₃ As ₁₈ S ₄₀ (Rathite I) | -4640523.52 + 2932.35·T | 298 - ? | [7] | formula uncertain |
| 9Pb + 13As + 14S ₂ (g) = Pb ₉ As ₁₃ S ₂₈ (Rathite II) | -3246695.9 + 2018.04·T | 298 - ? | [7] | formula uncertain |
| Cu + Pb + As + $\frac{3}{2}$ S ₂ (g) = CuPbAsS ₃ (Seligmannite) | -370029.38 + 191.25·T | 298 - 600 | [62] | |
| Cu + Pb + As + $\frac{3}{2}$ S ₂ (g) = CuPbAsS ₃ (Seligmannite) | -374844.2 + 205.57·T | 600 - 733 | [62] | |
| $\frac{1}{2}$ Cu ₂ S + $\frac{4}{3}$ PbS + $\frac{4}{3}$ As + S ₂ (g) = CuPbAsS ₃ | -374844.2 + 129.67·T | 298 - 377 | [7] | |
| $\frac{1}{2}$ Cu ₂ S + $\frac{4}{3}$ PbS + $\frac{4}{3}$ As + S ₂ (g) = CuPbAsS ₃ | -193484.59 + 136.45·T | 377 - 708 | [7] | |
| 6Cu + 3Zn + 4As + 6S ₂ (g) = Cu ₆ Zn ₃ As ₄ S ₁₂ (Nowackiite) | -1760260.51 + 797.92·T | 298 - ? | [7] | |
| Cu ₂ S + ZnS + $\frac{4}{3}$ As + S ₂ (g) = $\frac{1}{2}$ Cu ₆ Zn ₃ As ₄ S ₁₂ | -192860.76 + 124.85·T | 298 - 377 | [7] | |
| Cu ₂ S + ZnS + $\frac{4}{3}$ As + S ₂ (g) = $\frac{1}{2}$ Cu ₆ Zn ₃ As ₄ S ₁₂ | -196712.61 + 135.07·T | 377 - ? | [7] | |

Table 4. - (Continued.)

| | | | | |
|--|--------------------------------|-----------|------|--|
| $10\text{Cu} + 2\text{Zn} + 4\text{As} + \frac{13}{2}\text{S}_2(\text{g}) = \text{Cu}_{10}\text{Zn}_2\text{As}_4\text{S}_{13}$ (Zn-tennantite) | $-2119070 + 908.3 \cdot T$ | 298 – 693 | [63] | |
| $10\text{Cu} + 2\text{Zn} + 4\text{As} + \frac{13}{2}\text{S}_2(\text{g}) = \text{Cu}_{10}\text{Zn}_2\text{As}_4\text{S}_{13}$ (Zn-tennantite) | $-2130050 + 923.9 \cdot T$ | 693 - 875 | [63] | |
| $10\text{Cu} + 2\text{Zn} + 4\text{Sb} + \frac{13}{2}\text{S}_2(\text{g}) = \text{Cu}_{10}\text{Zn}_2\text{Sb}_4\text{S}_{13}$ (Zn-tetrahedrite) | $-2058151 + 903.2 \cdot T$ | 298 – 693 | [63] | |
| $10\text{Cu} + 2\text{Zn} + 4\text{Sb} + \frac{13}{2}\text{S}_2(\text{g}) = \text{Cu}_{10}\text{Zn}_2\text{Sb}_4\text{S}_{13}$ (Zn-tetrahedrite) | $-2,069,130 + 918.9 \cdot T$ | 693 – 903 | [63] | |
| $17\text{Pb} + 8\text{Sb} + 8\text{As} + \frac{41}{2}\text{S}_2(\text{g}) = \text{Pb}_{17}\text{Sb}_8\text{As}_8\text{S}_{41}$ (s) | $-5214100 + 2787 \cdot T$ | 298-600 | [7] | |
| $17\text{Pb} + 8\text{Sb} + 8\text{As} + \frac{41}{2}\text{S}_2(\text{g}) = \text{Pb}_{17}\text{Sb}_8\text{As}_8\text{S}_{41}$ (s) | $-5295900 + 3030 \cdot T$ | 600-? | [7] | |
| $16\text{Pb} + 9\text{Sb} + 9\text{As} + \frac{43}{2}\text{S}_2(\text{g}) = \text{Pb}_{16}\text{Sb}_9\text{As}_9\text{S}_{43}$ (s) | $-5375600 + 2939 \cdot T$ | 298-600 | [7] | |
| $16\text{Pb} + 9\text{Sb} + 9\text{As} + \frac{43}{2}\text{S}_2(\text{g}) = \text{Pb}_{16}\text{Sb}_9\text{As}_9\text{S}_{43}$ (s) | $-5452603 + 3169 \cdot T$ | 600-? | [7] | |
| $17\text{Pb} + 11\text{Sb} + 11\text{As} + 25\text{S}_2(\text{g}) = \text{Pb}_{17}\text{Sb}_{11}\text{As}_{11}\text{S}_{50}$ (s) | $-6169230 + 3853 \cdot T$ | 298-600 | [7] | |
| $17\text{Pb} + 11\text{Sb} + 11\text{As} + 25\text{S}_2(\text{g}) = \text{Pb}_{17}\text{Sb}_{11}\text{As}_{11}\text{S}_{50}$ (s) | $-6251040 + 4097 \cdot T$ | 600-? | [7] | |
| $12\text{Pb} + 5\text{Sb} + 5\text{As} + \frac{27}{2}\text{S}_2(\text{g}) = \text{Pb}_{12}\text{Sb}_5\text{As}_5\text{S}_{27}$ (s) | $-3474570 + 2022 \cdot T$ | 298-600 | [7] | |
| $12\text{Pb} + 5\text{Sb} + 5\text{As} + \frac{27}{2}\text{S}_2(\text{g}) = \text{Pb}_{12}\text{Sb}_5\text{As}_5\text{S}_{27}$ (s) | $-3532320 + 2194 \cdot T$ | 600-? | [7] | |
| $2\text{Pb} + \text{Sb} + \text{As} + \frac{5}{2}\text{S}_2(\text{g}) = \text{Pb}_2\text{SbAsS}_5$ (s) | $-632157 + 346.0 \cdot T$ | 298-600 | [7] | |
| $2\text{Pb} + \text{Sb} + \text{As} + \frac{5}{2}\text{S}_2(\text{g}) = \text{Pb}_2\text{SbAsS}_5$ (s) | $-641782 + 423.5 \cdot T$ | 600-? | [7] | |
| $5\text{Pb} + \text{Sb} + \text{As} + 4\text{S}_2(\text{g}) = \text{Pb}_5\text{SbAsS}_8$ (s) | $-1102840 + 537.8 \cdot T$ | 298-600 | [7] | |
| $5\text{Pb} + \text{Sb} + \text{As} + 4\text{S}_2(\text{g}) = \text{Pb}_5\text{SbAsS}_8$ (s) | $-1126910 + 609.3 \cdot T$ | 600-? | [7] | |
| $9\text{Cu} + \text{Bi} + 3\text{S}_2(\text{g}) = \text{Cu}_9\text{BiS}_6$ | $-792146.75 + 309.78 \cdot T$ | 673 - 923 | [64] | |
| $3\text{Cu} + \text{Bi} + \frac{3}{2}\text{S}_2(\text{g}) = \text{Cu}_3\text{BiS}_3$ | $-369531.16 + 168.1 \cdot T$ | 298 - 544 | [64] | |
| $3\text{Cu} + \text{Bi} + \frac{3}{2}\text{S}_2(\text{g}) = \text{Cu}_3\text{BiS}_3$ | $-380416.84 + 188.07 \cdot T$ | 544 – 783 | [64] | |
| $\text{Cu} + \text{Bi} + \text{S}_2(\text{g}) = \text{CuBiS}_2$ | $-232287.85 + 129.62 \cdot T$ | 298 - 544 | [64] | |
| $\text{Cu} + \text{Bi} + \text{S}_2(\text{g}) = \text{CuBiS}_2$ | $-243047.93 + 149.59 \cdot T$ | 544 - 758 | [64] | |
| $3\text{Cu} + 5\text{Bi} + \frac{9}{2}\text{S}_2(\text{g}) = \text{Cu}_3\text{Bi}_5\text{S}_9$ | $-1078624.35 + 711.08 \cdot T$ | 698 – 863 | [64] | |

Table 4. – (Continued.)

| | | | | |
|--|---------------------------------|------------|----------|--|
| $\text{Cu} + 3\text{Bi} + \frac{5}{2}\text{S}_2(\text{g}) = \text{CuBi}_3\text{S}_5$ | $-592277.28 + 413.11 \cdot T$ | 673 - 918 | [64] | |
| $6\text{Cu}_2\text{S} + \frac{4}{3}\text{Bi}_{\text{liq}} + \text{S}_2(\text{g}) = \frac{4}{3}\text{Cu}_9\text{BiS}_6$ | $-266900.13 + 229.14T$ | 708 - 923 | [7] | |
| $2\text{Cu}_2\text{S} + \frac{4}{3}\text{Bi} + \text{S}_2(\text{g}) = \frac{4}{3}\text{Cu}_3\text{BiS}_3$ | $-218220.20 + 136.78 \cdot T$ | 298 - 377 | [7] | |
| $2\text{Cu}_2\text{S} + \frac{4}{3}\text{Bi} + \text{S}_2(\text{g}) = \frac{4}{3}\text{Cu}_3\text{BiS}_3$ | $-225923.92 + 157.21 \cdot T$ | 377 - 544 | [7] | |
| $2\text{Cu}_2\text{S} + \frac{4}{3}\text{Bi}_{\text{liq}} + \text{S}_2(\text{g}) = \frac{4}{3}\text{Cu}_3\text{BiS}_3$ | $-240439.55 + 183.84 \cdot T$ | 544 - 708 | [7] | |
| $\frac{2}{3}\text{Cu}_3\text{BiS}_3 + \frac{4}{3}\text{Bi} + \text{S}_2(\text{g}) = 2\text{CuBiS}_2$ | $-218220.20 + 147.17 \cdot T$ | 298 - 544 | [7] | |
| $\frac{2}{3}\text{Cu}_3\text{BiS}_3 + \frac{4}{3}\text{Bi}_{\text{liq}} + \text{S}_2(\text{g}) = 2\text{CuBiS}_2$ | $-185479.43 + 173.79 \cdot T$ | 544 - 785 | [7] | |
| $\frac{1}{3}\text{Cu}_3\text{BiS}_3 + \frac{4}{3}\text{Bi}_{\text{liq}} + \text{S}_2(\text{g}) = \frac{1}{3}\text{Cu}_3\text{Bi}_5\text{S}_9$ | $-232735.84 + 174.33 \cdot T$ | 698 - 758 | [7] | |
| $\frac{1}{3}\text{Cu}_3\text{Bi}_5\text{S}_9 + \frac{4}{3}\text{Bi}_{\text{liq}} + \text{S}_2(\text{g}) = \text{CuBi}_3\text{S}_5$ | $-232735.84 + 176.10 \cdot T$ | 698 - 863 | [7] | |
| $6\text{Pb} + 2\text{Bi} + \frac{9}{2}\text{S}_2(\text{g}) = \text{Pb}_6\text{Bi}_2\text{S}_9$ | $-1269111.19 + 644.09 \cdot T$ | 298 - 544 | [65, 66] | > 400 °C composition changes to $\text{Pb}_9\text{Bi}_4\text{S}_{15}$ [65] |
| $6\text{Pb} + 2\text{Bi} + \frac{9}{2}\text{S}_2(\text{g}) = \text{Pb}_6\text{Bi}_2\text{S}_9$ | $-1290882.55 + 684.08 \cdot T$ | 544 - 600 | [65, 66] | |
| $8\text{Pb} + 6\text{Bi} + \frac{17}{2}\text{S}_2(\text{g}) = \text{Pb}_8\text{Bi}_6\text{S}_{17}$ | $-2303016.33 + 1335.17 \cdot T$ | 544 - 600 | [65, 66] | |
| $8\text{Pb} + 6\text{Bi} + \frac{17}{2}\text{S}_2(\text{g}) = \text{Pb}_8\text{Bi}_6\text{S}_{17}$ | $-2341534.89 + 1449.67T$ | 600 - 873 | [65, 66] | |
| $2\text{Pb} + 2\text{Bi} + \frac{5}{2}\text{S}_2(\text{g}) = \text{Pb}_2\text{Bi}_2\text{S}_5$ | $-640839.98 + 365.01 \cdot T$ | 298 - 544 | [65, 66] | |
| $2\text{Pb} + 2\text{Bi} + \frac{5}{2}\text{S}_2(\text{g}) = \text{Pb}_2\text{Bi}_2\text{S}_5$ | $-662611.34 + 404.99 \cdot T$ | 544 - 600 | [65, 66] | |
| $\text{Pb} + 2\text{Bi} + 2\text{S}_2(\text{g}) = \text{PbBi}_2\text{S}_4$ | $-484295.53 + 299.77 \cdot T$ | 298 - 544 | [65, 66] | |
| $\text{Pb} + 2\text{Bi} + 2\text{S}_2(\text{g}) = \text{PbBi}_2\text{S}_4$ | $-506066.89 + 330.21 \cdot T$ | 544 - 600 | [65, 66] | |
| $\text{Pb} + 4\text{Bi} + \frac{7}{2}\text{S}_2(\text{g}) = \text{PbBi}_4\text{S}_7$ | $-859985.47 + 592.89 \cdot T$ | 953 - 1003 | [65, 66] | |
| $4\text{PbS} + \frac{4}{3}\text{Bi} + \text{S}_2(\text{g}) = \frac{2}{3}\text{Pb}_6\text{Bi}_2\text{S}_9$ | $-218220.20 + 140.68 \cdot T$ | 298 - 544 | [7] | |
| $4\text{PbS} + \frac{4}{3}\text{Bi}_{\text{liq}} + \text{S}_2(\text{g}) = \frac{2}{3}\text{Pb}_6\text{Bi}_2\text{S}_9$ | $-232735.84 + 167.05 \cdot T$ | 544 - 873 | [7] | |
| $\frac{8}{15}\text{Pb}_6\text{Bi}_2\text{S}_9 + \frac{4}{3}\text{Bi}_{\text{liq}} + \text{S}_2(\text{g}) = \frac{2}{5}\text{Pb}_8\text{Bi}_6\text{S}_{17}$ | $-232735.84 + 169.23 \cdot T$ | 544 - 873 | [7] | |

Table 4. – (Continued.)

| | | | | |
|--|--------------------------------|------------|------|--|
| $\frac{2}{3}\text{Pb}_8\text{Bi}_6\text{S}_{17} + \frac{4}{3}\text{Bi} + \text{S}_2(\text{g}) = \frac{8}{3}\text{Pb}_2\text{Bi}_2\text{S}_5$ | $-217102.32 + 163.24 \cdot T$ | 298 - 544 | [7] | |
| $\frac{2}{3}\text{Pb}_8\text{Bi}_6\text{S}_{17} + \frac{4}{3}\text{Bi}_{\text{liq}} + \text{S}_2(\text{g}) = \frac{8}{3}\text{Pb}_2\text{Bi}_2\text{S}_5$ | $-231617.96 + 189.91 \cdot T$ | 544 - 698 | [7] | |
| $\frac{2}{3}\text{Pb}_2\text{Bi}_2\text{S}_5 + \frac{4}{3}\text{Bi} + \text{S}_2(\text{g}) = \frac{4}{3}\text{PbBi}_2\text{S}_4$ | $-218500.72 + 173.04 \cdot T$ | 298 - 994 | [7] | |
| $\frac{2}{3}\text{Pb}_2\text{Bi}_2\text{S}_5 + \frac{4}{3}\text{Bi}_{\text{liq}} + \text{S}_2(\text{g}) = \frac{4}{3}\text{PbBi}_2\text{S}_4$ | $-247531.99 + 196.95 \cdot T$ | 544 - 698 | [7] | |
| $\frac{2}{15}\text{Pb}_8\text{Bi}_6\text{S}_{17} + \frac{4}{3}\text{Bi}_{\text{liq}} + \text{S}_2(\text{g}) = \frac{16}{15}\text{PbBi}_2\text{S}_4$ | $-232735.84 + 174.21 \cdot T$ | 698 - 873 | [7] | |
| $\frac{2}{3}\text{PbBi}_2\text{S}_4 + \frac{4}{3}\text{Bi}_{\text{liq}} + \text{S}_2(\text{g}) = \frac{2}{3}\text{PbBi}_4\text{S}_7$ | $-250458.56 + 195.44 \cdot T$ | 953 - 1003 | [7] | |
| $\text{Cu} + \text{Pb} + \text{Bi} + \frac{3}{2}\text{S}_2(\text{g}) = \text{CuPbBiS}_3$ | $-389250.98 + 177.52 \cdot T$ | 298 - 544 | [67] | |
| $\text{Cu} + \text{Pb} + \text{Bi} + \frac{3}{2}\text{S}_2(\text{g}) = \text{CuPbBiS}_3$ | $-400136.66 + 197.49 \cdot T$ | 544 - 600 | [67] | |
| $2\text{Cu} + 2\text{Pb} + 4\text{Bi} + \frac{9}{2}\text{S}_2(\text{g}) = \text{Cu}_2\text{Pb}_2\text{Bi}_4\text{S}_9$ | $-1105825.99 + 566.89 \cdot T$ | 298 - 544 | [7] | |
| $2\text{Cu} + 2\text{Pb} + 4\text{Bi} + \frac{9}{2}\text{S}_2(\text{g}) = \text{Cu}_2\text{Pb}_2\text{Bi}_4\text{S}_9$ | $-1149586.42 + 646.86 \cdot T$ | 544 - 600 | [7] | |
| $\text{Cu} + \text{Pb} + 5\text{Bi} + \frac{9}{2}\text{S}_2(\text{g}) = \text{CuPbBi}_5\text{S}_9$ | $-1043915.78 + 612.78 \cdot T$ | 298 - 544 | [7] | |
| $\text{Cu} + \text{Pb} + 5\text{Bi} + \frac{9}{2}\text{S}_2(\text{g}) = \text{CuPbBi}_5\text{S}_9$ | $-1098344.18 + 712.72 \cdot T$ | 544 - 600 | [7] | |
| $2\text{Cu} + 5\text{Pb} + 5\text{Bi} + 14\text{S}_2(\text{g}) = \text{Cu}_2\text{Pb}_5\text{Bi}_5\text{S}_{14}$ | $-1783907.56 + 878.14 \cdot T$ | 298 - 544 | [7] | |
| $2\text{Cu} + 5\text{Pb} + 5\text{Bi} + 14\text{S}_2(\text{g}) = \text{Cu}_2\text{Pb}_5\text{Bi}_5\text{S}_{14}$ | $-1838335.96 + 978.08 \cdot T$ | 544 - 600 | [7] | |
| $\frac{2}{3}\text{Cu}_2\text{S} + \frac{4}{3}\text{PbS} + \frac{4}{3}\text{Bi} + \text{S}_2(\text{g}) = \frac{4}{3}\text{CuPbBiS}_3$ | $-218220.20 + 110.95 \cdot T$ | 298 - 377 | [7] | |
| $\frac{2}{3}\text{Cu}_2\text{S} + \frac{4}{3}\text{PbS} + \frac{4}{3}\text{Bi} + \text{S}_2(\text{g}) = \frac{4}{3}\text{CuPbBiS}_3$ | $-219111.99 + 118.11 \cdot T$ | 377 - 544 | [7] | |
| $\frac{2}{3}\text{Cu}_2\text{S} + \frac{4}{3}\text{PbS} + \frac{4}{3}\text{Bi} + \text{S}_2(\text{g}) = \frac{4}{3}\text{CuPbBiS}_3$ | $-233627.63 + 144.74 \cdot T$ | 544 - 708 | [7] | |
| $\frac{1}{3}\text{Cu}_2\text{S} + \frac{2}{3}\text{PbS} + \frac{4}{3}\text{Bi} + \text{S}_2(\text{g}) = \frac{1}{3}\text{Cu}_2\text{Pb}_2\text{Bi}_4\text{S}_9$ | $-218220.20 + 84.36 \cdot T$ | 298 - 377 | [7] | |
| $\frac{1}{3}\text{Cu}_2\text{S} + \frac{2}{3}\text{PbS} + \frac{4}{3}\text{Bi} + \text{S}_2(\text{g}) = \frac{1}{3}\text{Cu}_2\text{Pb}_2\text{Bi}_4\text{S}_9$ | $-219111.99 + 118.11 \cdot T$ | 377 - 544 | [7] | |
| $\frac{1}{3}\text{Cu}_2\text{S} + \frac{2}{3}\text{PbS} + \frac{4}{3}\text{Bi}_{\text{liq}} + \text{S}_2(\text{g}) = \frac{1}{3}\text{Cu}_2\text{Pb}_2\text{Bi}_4\text{S}_9$ | $-234016.10 + 156.34 \cdot T$ | 544 - 708 | [7] | |
| $\frac{2}{15}\text{Cu}_2\text{S} + \frac{4}{15}\text{PbS} + \frac{4}{3}\text{Bi} + \text{S}_2(\text{g}) = \frac{4}{15}\text{CuPbBi}_5\text{S}_9$ | $-216934.86 + 134.52 \cdot T$ | 298 - 377 | [7] | |

Table 4. – (Continued.)

| | | | | |
|--|---------------------------------|-----------|------|----------------------------------|
| $\frac{2}{15}\text{Cu}_2\text{S} + \frac{4}{15}\text{PbS} + \frac{4}{3}\text{Bi} + \text{S}_2(\text{g}) = \frac{4}{15}\text{CuPbBi}_5\text{S}_9$ | $-217441.46 + 135.90 \cdot T$ | 377 – 544 | [7] | |
| $\frac{2}{15}\text{Cu}_2\text{S} + \frac{4}{15}\text{PbS} + \frac{4}{3}\text{Bi}_{\text{liq}} + \text{S}_2(\text{g}) = \frac{4}{15}\text{CuPbBi}_5\text{S}_9$ | $-231957.09 + 162.49 \cdot T$ | 544 – 708 | [7] | |
| $\frac{1}{4}\text{Cu}_2\text{S} + \frac{5}{4}\text{PbS} + \frac{5}{4}\text{Bi} + \text{S}_2(\text{g}) = \frac{1}{4}\text{Cu}_2\text{Pb}_5\text{Bi}_5\text{S}_{14}$ | $-216717.14 + 118.40 \cdot T$ | 298 – 377 | [7] | |
| $\frac{1}{4}\text{Cu}_2\text{S} + \frac{5}{4}\text{PbS} + \frac{5}{4}\text{Bi} + \text{S}_2(\text{g}) = \frac{1}{4}\text{Cu}_2\text{Pb}_5\text{Bi}_5\text{S}_{14}$ | $-217680.11 + 120.96 \cdot T$ | 377 – 544 | [7] | |
| $3\text{Pb} + 2\text{Sb} + 3\text{S}_2(\text{g}) = \text{Pb}_3\text{Sb}_2\text{S}_6$ | $-833445.34 + 488.73 \cdot T$ | 883 – 903 | [68] | |
| $3\text{Pb} + 4\text{Sb} + \frac{11}{2}\text{S}_2(\text{g}) = \text{Pb}_5\text{Sb}_4\text{S}_{11}$ | $-1481038.63 + 809.43 \cdot T$ | 298 – 600 | [68] | |
| $5\text{Pb} + 4\text{Sb} + \frac{11}{2}\text{S}_2(\text{g}) = \text{Pb}_5\text{Sb}_4\text{S}_{11}$ | $-1505112.73 + 893.59 \cdot T$ | 600 – 873 | [68] | |
| $5\text{Pb} + 6\text{Sb} + 7\text{S}_2(\text{g}) = \text{Pb}_5\text{Sb}_6\text{S}_{14}$ | $-1853224.22 + 1131.15 \cdot T$ | 698 – 876 | [68] | |
| $6\text{Pb} + 10\text{Sb} + \frac{21}{2}\text{S}_2(\text{g}) = \text{Pb}_6\text{Sb}_{10}\text{S}_{21}$ | $-2682336.22 + 1613.38 \cdot T$ | 298 – 600 | [68] | Formula uncertain |
| $6\text{Pb} + 10\text{Sb} + \frac{21}{2}\text{S}_2(\text{g}) = \text{Pb}_6\text{Sb}_{10}\text{S}_{21}$ | $-2711225.14 + 1699.26 \cdot T$ | 600 – 853 | [68] | Formula uncertain |
| $\text{Pb} + 2\text{Sb} + 4\text{S}_2(\text{g}) = \text{PbSb}_2\text{S}_4$ | $-505074.62 + 310.20 \cdot T$ | 298 – 600 | [68] | Formula uncertain |
| $\text{Pb} + 2\text{Sb} + 2\text{S}_2(\text{g}) = \text{PbSb}_2\text{S}_4$ | $-509889.44 + 328.71 \cdot T$ | 600 – 818 | [68] | Formula uncertain |
| $\frac{5}{3}\text{PbS} + \frac{4}{3}\text{Sb} + \text{S}_2(\text{g}) = \frac{1}{3}\text{Pb}_5\text{Sb}_4\text{S}_{11}$ | $-232074.32 + 153.70 \cdot T$ | 298 – 883 | [7] | |
| $\frac{2}{3}\text{Pb}_5\text{Bi}_4\text{S}_{11} + \frac{4}{3}\text{Sb} + \text{S}_2(\text{g}) = \frac{2}{3}\text{Pb}_5\text{Sb}_6\text{S}_{14}$ | $-232074.32 + 102.54 \cdot T$ | 698 – 876 | [7] | |
| $\frac{12}{39}\text{Pb}_5\text{Bi}_4\text{S}_{11} + \frac{4}{3}\text{Sb} + \text{S}_2(\text{g}) = \frac{10}{39}\text{Pb}_6\text{Sb}_{10}\text{S}_{21}$ | $-232074.32 + 160.77 \cdot T$ | 298 – 698 | [7] | |
| $\frac{2}{3}\text{Pb}_6\text{Bi}_{10}\text{S}_{21} + \frac{4}{3}\text{Sb} + \text{S}_2(\text{g}) = \frac{4}{3}\text{Pb}_6\text{Sb}_{10}\text{S}_{21}$ | $-232074.32 + 165.25 \cdot T$ | 298 – 818 | [7] | |
| $3\text{Cu} + \text{Sb} + \frac{3}{2}\text{S}_2(\text{g}) = \text{Cu}_3\text{SbS}_3$ | $-379922.79 + 170.65 \cdot T$ | 298 – 881 | [69] | |
| $\text{Cu} + \text{Sb} + \text{S}_2(\text{g}) = \text{CuSbS}_2$ | $-242679.49 + 130.04 \cdot T$ | 298 – 826 | [69] | |
| $3\text{Cu} + \text{Sb} + 2\text{S}_2(\text{g}) = \text{Cu}_3\text{SbS}_4$ | $-466957.99 + 244.05 \cdot T$ | 298 – 900 | [69] | |
| $12\text{Cu} + 4\text{Sb} + \frac{13}{2}\text{S}_2(\text{g}) = \text{Cu}_{12}\text{Sb}_4\text{S}_{13}$ | $-1606717.99 + 725.91 \cdot T$ | 298 – 816 | [69] | composition not well represented |

Table 4. – (Continued.)

| | | | | |
|--|---------------------------------|-----------|-----|--|
| $\frac{2}{3}\text{Cu}_2\text{S} + \frac{4}{3}\text{Sb} + \text{S}_2(\text{g}) = \frac{4}{3}\text{Cu}_3\text{SbS}_3$ | $-232078.51 + 140.22 \cdot T$ | 298 – 377 | [7] | |
| $\frac{2}{3}\text{Cu}_2\text{S} + \frac{4}{3}\text{Sb} + \text{S}_2(\text{g}) = \frac{4}{3}\text{Cu}_3\text{SbS}_3$ | $-239782.22 + 160.65 \cdot T$ | 377 – 708 | [7] | |
| $\frac{4}{3}\text{Cu}_3\text{SbS}_3 + \frac{4}{3}\text{Sb} + \text{S}_2(\text{g}) = 2\text{CuSbS}_2$ | $-232078.51 + 146.33 \cdot T$ | 298 – 816 | [7] | |
| $2\text{Cu}_3\text{SbS}_3 + \text{S}_2(\text{g}) = 2\text{Cu}_3\text{SbS}_4$ | $-174053.65 + 159.52 \cdot T$ | 298 – 861 | [7] | |
| $8\text{Cu}_3\text{SbS}_3 + \text{S}_2(\text{g}) = 2\text{Cu}_{12}\text{Sb}_4\text{S}_{13}$ | $-174053.65 + 137.50 \cdot T$ | 298 – 813 | [7] | |
| $\text{Cu} + \text{Pb} + \text{Sb} + \frac{3}{2}\text{S}_2(\text{g}) = \text{CuPbSbS}_3$ | $-399642.62 + 192.43 \cdot T$ | 298 – 600 | [7] | |
| $\text{Cu} + \text{Pb} + \text{Sb} + \frac{3}{2}\text{S}_2(\text{g}) = \text{CuPbSbS}_3$ | $-404457.44 + 206.74 \cdot T$ | 600 – ? | [7] | |
| $\text{Cu} + 13\text{Pb} + 7\text{Sb} + 12\text{S}_2(\text{g}) = \text{CuPb}_{13}\text{Sb}_7\text{S}_{24}$ | $-3327534.66 + 1656.09 \cdot T$ | 298 – 600 | [7] | |
| $\text{Cu} + 13\text{Pb} + 7\text{Sb} + 12\text{S}_2(\text{g}) = \text{CuPb}_{13}\text{Sb}_7\text{S}_{24}$ | $-3390127.32 + 1842.19 \cdot T$ | 600 – ? | [7] | |
| $\frac{2}{3}\text{Cu}_2\text{S} + \frac{4}{3}\text{PbS} + \frac{4}{3}\text{Sb} + \text{S}_2(\text{g}) = \text{CuPbSbS}_3$ | $-232078.51 + 131.21 \cdot T$ | 298 – 377 | [7] | |
| $\frac{2}{3}\text{Cu}_2\text{S} + \frac{4}{3}\text{PbS} + \frac{4}{3}\text{Sb} + \text{S}_2(\text{g}) = \text{CuPbSbS}_3$ | $-233137.77 + 137.10 \cdot T$ | 377 – 708 | [7] | |
| $\frac{2}{3}\text{Cu}_2\text{S} + \frac{4}{3}\text{PbS} + \frac{4}{3}\text{Sb} + \text{S}_2(\text{g}) = \text{CuPbSbS}_3$ | $-236039.22 + 139.88 \cdot T$ | 708 – ? | [7] | |
| $\frac{2}{21}\text{Cu}_2\text{S} + \frac{51}{21}\text{PbS} + \frac{4}{3}\text{Sb} + \text{S}_2(\text{g}) = \text{CuPb}_{13}\text{Sb}_7\text{S}_{24}$ | $-232074.32 + 132.55 \cdot T$ | 298 – 377 | [7] | |
| $\frac{2}{21}\text{Cu}_2\text{S} + \frac{51}{21}\text{PbS} + \frac{4}{3}\text{Sb} + \text{S}_2(\text{g}) = \text{CuPb}_{13}\text{Sb}_7\text{S}_{24}$ | $-232442.76 + 133.52 \cdot T$ | 377 – 708 | [7] | |

4 Discussion

Craig and Barton [7] derived approximate temperature dependent Gibbs energies of formations for a large number of sulfosalts, based on an assumption of near –ideal mixing of the simple sulfide end members to produce sulfosalts of intermediate composition, as expressed in Equation (1).

$$\Delta_f G_m^0(\text{sulfosalt, J/mol}) = [\sum_1^n (N_1 \Delta_f G_m^0(\text{sulfide}) + \dots N_i \Delta_f G_m^0(\text{sulfide}))] + (5.02 \pm 3.35) \cdot (R \cdot T(K) \cdot \sum N_i \ln N_i), \quad (1)$$

where N_i is mole fraction of a component sulfide in the formation reaction. Their approach is based on the experimental work of [8], who found that an average value of the Gibbs energies of mixing (ΔG_{mix}) of reactions from the end-member sulfides for more than 20 different sulfosalts were very small, about $-1884.06 + 1465.38$ J/equivalent. In their estimates of ΔG_{mix} , they assumed $\Delta H_{mix}^o = 0$ and

$$\Delta S_{mix}^o = (5.02 \pm 3.35) \cdot (R \cdot T(K) \cdot \sum N_i \ln N_i). \quad (2)$$

In the absence of enthalpy data for sulfosalts their ideal mixing model did not include a heat of mixing term, though as they also noted that the heat of mixing needs not to be zero.

In fact, our experimental results on the Gibbs energies of formation of AgBi_3S_5 (pavonite) [70] have enabled us to assess the Craig and Barton's model quantitatively. Based on our enthalpy data for the formation of AgBi_3S_5 (pavonite) from the pure elements at their standard state (Equation (3)) the assumption of zero enthalpy of mixing made by Craig and Barton [7] (Equation (4)) may be a reasonable approximation.

$$- 234.99 + 0.0041 \cdot T(K) \quad (299 - 460 \text{ K, kJ/mol}) \quad (3)$$

$$- 232.04 + (0.00165 \pm 0.00175) \cdot T(K) \quad (298 - 460 \text{ K, kJ/mol}) \quad (4)$$

In Table 4, not all sulfidation reactions are known to represent stable equilibria, such data are marked by the word 'uncertain formula'. Equations

for some of the Gibbs energies of formations and reactions were obtained by linear fitting and extrapolation of experimental data, within the temperature ranges of phase stabilities.

Thermal stabilities of some pure sulfides and sulfosalts in the Cu-(As, Bi, Pb, Sb, Se, Te, Nb, Zn, Mo)-S and Ni-(As, Se)-S systems are also reviewed and compiled in an organized manner (see Appendix).

5 Summary and Conclusions

Thermodynamic properties of some equilibrium phases in the Ni-(As, Se)-S and Cu-(As, Bi, Pb, Sb, Se, Te, Nb, Zn, Mo)-S systems were compiled and reviewed, based on available literature. Particular emphasis was given to the compilation and refining of data for the standard Gibbs energies of formations of equilibrium phases which are of interest in the pyrometallurgy of copper and nickel production. Phase stabilities, phase relations and solubility limits of some equilibrium phases in the Ni-(As, Se)-S and Cu-Mo-Bi-Nb-S systems were reviewed. Thermal stabilities of some pure sulfides and sulfosalts (including the previous studies) were also compiled (see Appendix).

Experimental thermochemical data of the ternary and quaternary sulfidic phases are rare or unavailable in the literature. Thermochemical data of most binary sulfides in the multi-component systems are relatively well established. Gibbs energies of formations of some binary and ternary phases, mostly as a sulfidation reaction, have been reviewed and collected in Table 4.

Earlier reports [3, 5, 6] are also reviewed, updated, and extended, whenever necessary. The Gibbs energies of formations and reactions are mostly presented as linear equations, in each temperature ranges of phase stabilities.

Acknowledgements

The authors are grateful to Improved Sulfide Smelting (ISS) project of the ELEMET program and Tekes, the Finnish Funding Agency for Technology and Innovation, for financial support. This work was made as a sub task of ISS, supported financially also by Boliden Harjavalta Oy, Boliden Kokkola Oy, Norilsk Nickel Finland Oy and Outotec (Finland) Oy.

References

1. Craig, J. R. and Kullerud, G. The Cu-Zn-S System, *Mineral. Deposita (Berl.)* 8 (1973), 81 – 91.
2. Latvalahti, U., Cu-Pb-Zn Ores in the Aijala-Orijarvi Area, Southwest Finland, *Economic Geology*, Vol. 74 (1979), 1035 - 1059.
3. Tesfaye Firdu, F. & Taskinen, P.: Sulfide Mineralogy - Literature Review, Aalto University Publications in Materials Science and Engineering, Espoo, TTK-MT-214 (2010), 51 p. ISBN 978-952-60-3271-9.
4. Hietanen, P., Epäpuhtaussulfidisysteemien tasapainot ja termodynamiikka sekä Ag-Te-systeemin tutkiminen emf-tekniikalla, Diplomityö, Aalto-yliopiston teknillinen korkeakoulu, Materiaalitekniikan tutkinto-ohjelma, Espoo (2010), 66 s.
5. Tesfaye Firdu, F. and Taskinen, P., Thermodynamics and Phase Equilibria in the (Ni, Cu, Zn)-(As, Sb, Bi)-S Systems at Elevated Temperatures (300 – 900 °C), Aalto University Publications in Materials Science and Engineering, Espoo, TTK-MT-216 (2010), 51 p. ISBN 978-952-60-3271-9.
6. Tesfaye, F. and Taskinen, P., Phase Equilibria and Thermodynamics of the Systems Zn-As-Cu-Pb-S at Temperatures below 1173.15 K, Aalto University publication series SCIENCE + TECHNOLOGY 7/2011, 51 p. ISBN (printed) 978-952-60-4125-4, ISBN (pdf) 978-952-60-4126-1
7. Craig, J. R. and Barton Jr., P. B., Thermochemical approximations for sulfosalts, *Economic Geology* 68 (1973), 493 – 506.
8. Craig, J. R. and Lees, W. R., Thermochemical Data for Sulfosalts Ore Minerals, Formation from Simple Sulfides, *Eco. Geo.*, Vol. 67 (1972), 373 – 377.
9. MTDATA—phase diagram software from the national physical laboratory, SGTE Pure Element Transition Data. Available: <http://mtdata.software.googlepages.com/unarytable.html> [Accessed: 20.07.2011].

10. Lee, S. Y. and Nash, P., Ni-Se (Nickel-Selenium), Alloy Phase Diagrams, Binary Alloy Phase Diagrams, ASM, Vol. 3 (1992), 2857 - 2859.
11. Kuznecov, K., Eliseev, A., Spak, Z. Palkina, K., Sokolova, M. and Dmitriev, A., The Phase Diagram of the System Ni-Se, Proc. 4th All-Union Conf. on Semiconductor Materials, Moscow, U.S.S.R., (1961), 159 – 173. (In Russian; TR: Consultants Bureau, New York (1963), 128 - 139.)
12. Massalski, Thaddeus B., Binary Alloy Phase Diagrams, ASM, Vol. 3, 2nd edition (1990), 2105 - 3542.
13. Degterov, S.A., Pelton, A.D. and L'Ecuyer, J.D., Thermodynamic Optimization of the Selenium-Arsenic (Se-As) System, Journal of Phase Equilibria Vol. 18, No. 4 (1997), 357 – 368.
14. Drowart, J., Smoes, S., Auwera-Mahieu, A.M.V. and Trio, E., Proc. Third Int. Syrup. on Industrial Uses of Selenium and Tellurium, 15-17 Oct., Saltsjobaden, Stockholm, Sweden, 323 (1984).
15. Dembovsky, S.A. and Luzhnaya, N.P., As–Se Phase Diagram, Russ. J. Inorganic Chem., vol. 3, 9 (1964), 1583-1589. (Original paper in Russian: Neorg. Khim., 9 (3) (1964), 660-664.)
16. Blachnik, R., Hoppe, A. and Wickel, U., Die Systeme Arsen-Schwefel und Arsen-Selen und die thermodynamischen Daten ihrer Verbindungen, Z. Anorg. Allg. Chem., 463 (1980) 78-90. (in German)
17. Myers, M.B. and Felty, E.J., 'Structural characterizations of vitreous inorganic polymers by thermal studies', Mater Res. Bull., 2(7) (1967), 535 - 546.
18. O'Hare, P.A.G., Lewisc, Brett M., Susman, S. and Volin, K.J., Standard molar enthalpies of formation and transition at the temperature 298.15 K and other thermodynamic properties of the crystalline and vitreous forms of arsenic sesquiselenide (As₂Se₃) Dissociation enthalpies of As-Se bonds, J. Chem. Therm. Vol. 22, Issue 12 (1990), 1191-1206.
19. Steblevskii, A.V., Alikhanyan, A. S., Gorgoraki, V. I. and Pashinkin, A. S., Heats of Formation of Arsenic Sulfides, Russian Journal of Inorganic Chemistry, Vol. 31, No. 7, pp. 945-947, 1986.
20. Sharma, R.C., Chang, Y.A., Binary Alloy Phase Diagrams, ASM, Vol. 3, 2nd edition (1992), 3278 - 3279.

21. Ringer, W.E., Mischkrystalle von Seliwefel mit Selen, *Z. Anorg. Allg. Chem.*, 32 (1902) 183-218. (In German)
22. Sharma, R.C., Chang, Y.A., The S-Se (Sulfur-Selenium) System, *Journal of Phase Equilibria* Vol. 17, No. 2 (1996), 148.
23. Boudreau, R. A and Haendler, H. M., "The Isostructural Sulfur. Phase of Selenium-Sulfur, Se_nS_{8-n} ," *J. Solid State Chem.*, 36 (1981) 289 – 296.
24. Geller, S. and Lind, M. D., "Pressure-Induced Phase of Sulfur-Selenium," *Science*, 155 (1967) 79 – 80.
25. Zhukov, E. G., Dzhabaridze, O. I., Dembovskii, S. A. and Popova, N. P., System As_2S_3 – As_2Se_3 , *Izv. Akad. Nauk. SSSR, Neorg. Mater.*, 1974, vol. 10, 10 (1974), 1886-1887; *Inorg. Mater. (Engl. Transl.)*, vol. 10, 10 (1974) 1619-1620.
26. ACerS-NIST, Phase Equilibria Diagrams, CD-ROM Database, Version 3.3, NIST Standard Reference Database 31, National Institute of Standards and Technology (NIST), The American Ceramic Society (2010).
27. Myers, M.B. and Felty, E.J., 'Structural characterizations of vitreous inorganic polymers by thermal studies,' *Mat. Res. Bull.*, 2(7) (1967), 535-546.
28. Subramanian, P. R. and Laughlin, D.E., The Cu-Mo (Copper-Molybdenum) System, *Binary Alloy Phase Diagrams*, 2nd Ed., Ed. T.B. Massalski 2 (1990) 1435–1438.
29. Brewer, L. and Lamoreaux, R.H., Mo-S (Molybdenum-Sulfur), *Alloy Phase Diagrams, Binary Alloy Phase Diagrams, ASM, Vol. 3* (1992), 2660 - 2661.
30. Chang, Y.A, Neumann, J.P. & Choudary, U. V., *Phase Diagrams and Thermodynamic Properties of Ternary Copper-Sulfur-Metal Systems*, *Inra Monograph VII, The Metallurgy of Copper* (1979), 191 p.
31. Stemprok, M., *The Bi-Mo-S System*, Carnegie Institution, 336 -338.
32. Noddack, I. and Noddack, W., *Die geochemie des rheniums. Z. Physik. Chem. A154* (1931), 207-244.
33. Grover, B., *Phasengleichgewichtsbeziehungen im System Cu-Mo-S in Relation zu natürlichen Mineralien*, *Neues Jahrb. Mineral., Monatsh.*, 1965, 219.

34. Grover, B. and Moh, G. H., "Phasengleichgewichtsbeziehungen im System Cu-Mo-S in Relation zu natürlichen Mineralien," Neues Jahrb. Mineral., Monatsh., 1969, 529.
35. Biltz, W. and Kocher, A., über das System Niobschwefel, Z. Anorg. Chem. 237, 369 (1938).
36. Jellinek, F., The System Niobium-Sulfur, Ark. Kemi. 20, 447 (1963).
37. Jellinek, F., Brauer, G. and Müller, H., Molybdenum and Niobium Sulphides, Nature, 185 (1960), 376-377.
38. Hodouin, D. and Meta, U., The Standard Free Energy of Formation of Niobium Sulfides, Met. Trans. B, 6B (1975), 223.
39. Hartman, H. and Wagner, G., determination of the heats of combustion of some sulfides of the 5th and 6th subgroups with a new high-temperature differential calorimeter, Abh. Braunsch. Wiss. Ges. 14, 13 (1962).
40. Mishchenko, A. V., Yushina, I. V. and Fedorva, V. E., Zhurnal Neorganicheskoi Khimii, 33 (2) (1988), 437 - 442. (In Russian). Translation: Russian Journal of Inorganic Chemistry, vol. 33, 2 (1988), 244 - 247.
41. Chen, H. Y., Tuenge, R. T. and Franzen, H. F., Preparation and Crystal Structure of Nb₁₄S₅, Inorg. Chem., vol. 12, 3 (1973), 552 - 555.
42. Kadijk, F. and Jellinek, F., The System Niobium-Sulfur, J. Less-Common Met., 19 (1969), 421 - 430.
43. Van Arkel, A. E., and Crevecoeur, C., Quelques sulfures et Séléniures Complexes, J. Less-Common Metals, vol. 5, 2 (1963), 177 - 180.
44. Lynch, D. C., A review of the physical chemistry of arsenic as it pertains to primary metals production, Arsenic Metallurgy Fundamentals and Applications: proceedings of a symposium sponsored by the TMS-AIME Physical Chemistry Committee, the 1988 TMS annual meeting and exhibition (1988), 3 - 33.
45. Itagaki, K. and Nishimura, T., Thermodynamic Properties of Compounds and Aqueous Species of VA elements, Metallurgical Review of MMIJ, 3(2) (1986), 29 - 48.
46. Babanly, M. B., Salimov, Z. E., Babanly N. B. and Imamalieva, S. Z., Thermodynamic Properties of Copper Thallium Tellurides, Inorganic Materials, vol. 47, No. 4 (2011) 361 - 364.

47. Lau, K. H., Lamoreaux, R. H. and Hildenbrand, D. L., Vapor Pressure Determination of Arsenic Activity in a Molten Cu-Fe-S Matte, *Metallurgical and Materials Transactions B*, 14B (1983), 253 – 258.
48. Mah, A. D., Thermodynamic data for arsenic sulfide reactions, Bureau of Mines Report of Investigation 8671 (1982).
49. Hino, M., Toguri, J. M. and Nagomori, The Gibbs Free Energy of Gaseous AsS, *Canadian Metallurgical Quarterly*, 25 (1986), 195 – 197.
50. Barin, I., Knacke, O. and Kubaschewski, O., *Thermochemical Properties of Inorganic Substances*, FRG: Springer-Verlag, Berlin (1977).
51. Lynch, D. C., “Standard Free Energy of Formation of NiAsS,” *Metallurgical Transactions B*, 13B (1982), 285 – 288.
52. Shigematsu, K., “Vapor Pressure Measurements of Arsenic Compounds,” *Metallurgical Review of MMIJ*, 3(2) (1986), 49 – 64.
53. Lin, R. Y., Hu, D. C. and Chang, Y. A., The nickel-sulfur system, *Metall. Trans. B*, Vol. 9B (1978), 531 – 38.
54. Sharma, R. C. and Chang, Y. A., Thermodynamics and phase relationships of transition metal-sulfur systems: IV. thermodynamic properties of the Ni-S liquid phase and the calculation of the Ni-S phase diagram, *Metall. Trans. B*, vol. 11B (1980), 139 – 146.
55. Schoonmaker, Richard C. and Lemmerman, Keith J., Vaporization of Zn₃As₂, *Journal of Chemical and Engineering Data*, vol. 17, No. 2 (1972), 139 – 143.
56. Ferro, R. and Marazza, R., The As - Mo system, *Bulletin of Alloy Phase Diagrams*, 1, (2) (1980), 76 – 78.
57. Pankratz, L. B., Mah, A. D. and Watson, S. W.; Thermodynamic properties of sulfides, United States Department of the Interior Bureau of Mines, Bulletin 989 (1989).
58. Shatynski, Stephen R.; The Thermochemistry of Transition Metal Sulfides, *Oxidation of Metals*, Vol. 11, No. 6 (1977), 307 – 320.
59. Maske, S. and Skinner, B.J., Studies of the sulfosalts of copper, I, Phases and Phase Relations in the System Cu-As-S. *Economic Geology*, 66 (1971), 901–918.
60. Wernick, J. H. and Benson, K. E., New semiconducting ternary compounds, *Journal of Physics and Chemistry of Solids* 3 (1957), 157.

61. Roland, G. W., The System Pb-As-S - Composition and Stability of Jordanite, *Mineral. Deposita (Berl.)*, Vol. 3, (1968), 249 - 260.
62. Wernick, J.H., Geller, S., Benson, K. E., New Semi Conductors, *J. Phys. Chem. Solids* 4 (1958), 154-155.
63. Robert, R. Seal II, Eric J. Essene and William, C. Kelly., Tetrahedrite and Tennantite, Evaluation of Thermodynamic Data and Phase Equilibria. *Canadian Mineralogist*, vol. 28. 1990. 725- 738.
64. Sugaki, A., Shima, H., Phase relations of the Cu₂S-Bi₂S₃ system. *Techn. Report Yamaguchi University* 1 (1972) 45-70.
65. Craig, J. R., Phase relations and mineral Assemblages in the Ag-Bi-Pb-S system. *Mineral Deposita*, I (1967), 278-306.
66. Weissburg, B. G., Getchellite, AsSbS₃, a New Mineral from Humboldt County, Nevada, *American Mineralogist*, 50 (1965) 1817 – 1826.
67. Springer, G., The synthetic Solid – Solution Series Bi₂S₃-BiCuPbS₃. (bismuthinite-aikinite). *Neues Jahrb Mineral. Monatsh.* (1971), 19-27.
68. Craig, J. R., Chang, L. L. Y. & Lees, W. R., Investigations in the Pb-Sb-S System, *Can. Mineral.* 12 ((1973)), 199-206.
69. Skinner, B.J., Luce, F. & E., Makovitsky, Studies of the Sulphosalts of Copper III. Phase Relations in the System Cu-Sb-S. *Econ. Geologist*, 67 (1972), 924-938.
70. Tesfaye, F. and Taskinen, P., Experimental Thermodynamic Study of the Equilibrium Phase Assemblage AgBi₃S₅-Bi₂S₃-S, TMS2012 - International Smelting Technology Symposium (Incorporating the 6th Advances in Sulfide Smelting Symposium), A print-only volume (2012), Orlando, USA. (Accepted)
71. Andrew, G., Tomkins, B., Ronald, Frost & David, R.M., Pattison, Arsenopyrite Melting During Metamorphism of Sulfide Deposits. *The Canadian Mineralogist*. Vol. 44 (2006), 1045 – 1062.
72. Yund, R. A., The System Ni-As-S: Phase Relations and Mineralogical Significance. *American Journal of Science*, vol. 260 (1962), 761-782.
73. Emelina, A. L., Alikhanian, A. S., Steblevskii, A. V. and Kolosov, E. N., Phase Diagram of the As-S system, *Inorganic materials* vol. 43, No. 2 (2007), 95-104.
74. Massalski, Thaddeus, B., *Binary Alloy Phase Diagrams*, ASM, Vol. 1, 2nd edition (1990), 1- 970.

75. Kullerud, G., The Lead-Sulfur System: American Journal of Science, v. 267-A (1969), 233–256.
76. Chang, L. L. Y. & Bever, J. E., Lead Sulfosalt Minerals: Crystal Structures, Stability, Relations, and Paragenesis, Mineral Science Engineering, vol. 5, No. 3 (1973), 181 – 191.
77. Kutolglu, A., Röntgenographische und thermische Untersuchungen im quasibinären System PbS-As₂S₃. Neues Jahrbuch für Mineralogie. Monatshefte 2 (1969), 68-72.
78. Rösch, H.; Hellner, E., Hydrothermale Untersuchungen am System PbS-As₂S₃. Naturw. 46 (1959), p. 72.
79. Le Bihan, M.-T. & Petiau, J., Contribution à l'étude structurale des cristallines de la rathite-III. C. R. Acad. Sci. 251 (20) (1963), 2196-2198.
80. Burkart-Baumann, I., Vanadium: Element and geochemistry. in Fairbridge, R. W. (ed.) The Encyclopedia of Geochemistry and Environmental Sciences, Encyclopedia of Earth Sciences Series, 4A (1972), 1234–1237, Dowden, Hutchinson & Ross Inc., Stroudsburg, Pennsylvania.
81. Fleet, M., Phase Equilibria at High Temperature, Sulfide Mineralogy and Geochemistry, Reviews in Mineralogy and Geochemistry, vol. 61 (2006), 365 - 419.
82. Gaines, R., Luzonite, Famatinite and Some Related Minerals, Amer. Mineral., 42 (1957), 772.
83. Kurz, G. & Blachnik, R., New aspects of the system Cu-As-S, J. Less-Common Metals, 155 (1) (1989), 1 – 8.
84. Müller, A., Reaktivität im System Kupfer-Arsen-Schwefel und in den Entsprechenden Randsystemen. Ph.D. Thesis. Universität Osnabrück, Fachbereich Biologie/Chemie. 2000. 182 P.
85. Bayliss, P., A further crystal structure refinement of gersdorffite. Am. Mineral. 67 (1982), 1058-1064.
86. Clark, A. H. & Sillitoe, R. H., Cuprian sphalerite and a probable copper-zinc sulfide, Cachiyuyo de Llampos, Copiapó, Chile, The American Mineralogist, vol. 55 (1970), 1021 - 1025.
87. Craig, J. R., Kullerud, G., Phase relations and mineral assemblages in the copper-lead-sulfur System. Amer. Mineral., 53 (1968), 145-161.

88. Schüller, A. & Wohlmann, E., Betehtinit, ein neues blei-kupfer-sulfid aus den Mansfelder Rücken, *Geologie*, 4 (1955), 535-555.
89. Okamoto, H., *Phase Diagrams for Binary Alloys*, ASM International: Materials Park, OH, Desk handbook (2000).
90. Karup-Moller, S. & Makovicky, E. Skinnerite, Cu_3SbS_3 , a New Sulfosalt from the Ilimaussaq Alkaline Intrusion, South Greenland, *American Mineralogist*, Vol. 59 (1974) 889 - 895.
91. Lin, J. C., Sharma, R. C., and Chang, Y. A., The Bi-S (Bismuth-Sulfur) System, *Journal of Phase Equilibria*. Vol. 17, 2 (1996), 132 – 139.
92. Daqing, Wu., Phase Relations in the Systems $\text{Ag}_2\text{S-Cu}_2\text{S-PbS}$ and $\text{Ag}_2\text{S-Cu}_2\text{S-Bi}_2\text{S}_3$ and their Mineral Assemblages, *Geochemistry*, vol. 6, 3 (1987), 216-224.
93. Moore, D. E. and Dixon, F. W., Phases of the System $\text{As}_2\text{S}_3\text{-Sb}_2\text{S}_3$, *Trans., Am. Geophys. Union* 54 (1973), 1223 – 1224.
94. Craig, J. R., Skinner, R., Francis, C. A., Luce, E.D. and Makovicky, M., Phase Relations in the As-Sb-S System, *Eos*, 55 (1974), 483.
95. Dickson F.W., Radtke A.S., Wiessberg, B.G. and Heropoulos, C., Solid Solution of Antimony, Arsenic, and Gold in Stibnite (Sb_2S_3), Orpiment (As_2S_3) and Realgar (As_2S_2). *Economic Geology*, 70 (1975), 591-594.
96. Radtke, A. S., Preliminary geologic map of the Carlin gold mine, Eureka County, Nevada. U.S. Geol. Surv. Misc. Field Studies Map MF-537 (1973).
97. Hayase, K., Minerals Bismuthinite-Stibnite Series, with special reference to horobetsuite from Horobetsu mine, Hokkaido, Japan. *Mineral. Jour.*, 1 (1955), 189-197.
98. Springer, G. and Laflamme, J.H.G., The system $\text{Bi}_2\text{S}_3\text{-Sb}_2\text{S}_3$, *Canadian Mineralogist*, 10 (1971), 847-853.
99. Kyono, A. and Kimata, M., Structural Reinvestigation of Getchellite $\text{As}_{0.98}\text{Sb}_{1.02}\text{S}_{3.00}$, *American Mineralogist*, vol. 89 (2004), 696-700.
100. Kato, A., Ikunolite a New Bismuth Mineral from the Ikuno Mine, Japan, *Mineral J. Japan* 2 (1959), 397 – 407.
101. Markham, N. L., Plumbian ikunolite from Kingsgate, New South Wales, *Am. Mineral* 47 (1962), 1431 – 1434.

102. Godovicov, A. A. and IL'yasheva, N. V., Phase Diagram of a Bismuth – Bismuth Sulfide – Bismuth Selenide System, Materialy po Geneticheskoi I Eksperimental' noi Mineralogii 6 (1971), 5 -14.
103. Belgaryan, M.L. and Abrikasov H. K., The Bi_2Te_3 - Bi_2Se_3 System, Dokl Akad Nauk USSR 129 (1959), 135.
104. Godovicov, A. A., Kochetkova, K. V. and Lavrent'ev, YuG, Bismuth Sulfotelluride form the Sokhondo Deposit, Geologiya I Geofizika 11 (1970), 123 – 127.
105. Yusa, K., Kitakaze, A. and Sugaki, A., Synthesized Bismuth-Tellurium-Sulfur System, Synthetic Sulfide Minerals, Science Reports Tohoku University

Appendix

Summary of some studies on the thermal stabilities (T_{max}) of sulfides and sulfosalts, at 1 atm., in the Cu-As-Bi-Pb-Sb-Se-Te-Nb-Zn-Mo-S and Ni-As-Se-S systems.

| System | Chemical formula (mineral name) | T_{max} (°C) | Ref. | |
|---|--|----------------|---------------------|------------------------|
| Pb-As-S | α AsS (realgar) | 0 - 266 | [71, 72, 73, 74] | |
| | β AsS | 266 - 319 ± 2 | | |
| | As ₂ S ₃ (orpiment) | 310 ± 2 | | |
| | α As ₄ S ₃ (dimorphite) | 0 - 131 | | |
| | β As ₄ S ₃ | 131 - 151 | | |
| | γ As ₄ S ₃ | 151 - 212 ± 2 | [75] | |
| | PbS (galena) | 1115 | | |
| | Pb ₉ As ₄ S ₁₅ (Gratonite) | 250 | | [76, 77, 78, 79,80] |
| | Pb ₉ As ₄ S ₁₅ (Jordanite) | 549 | | |
| | Pb ₂ As ₂ S ₅ (Dufrenoyite) | 485 ? | | |
| | Pb ₁₉ As ₂₆ S ₅₈ (Rathite II) | 474 | | |
| PbAs ₂ S ₄ (Sartorite) | 305 | | | |
| Pb ₃ As ₄ S ₉ (Baumhauerite) | 458 | [77] | | |
| Cu-As-S | Cu ₂ S / monoclinic (chalcocite) | 103 | [81] | |
| | Cu ₂ S / hexagonal | 103 ~435 | | |
| | Cu ₂ S / cubic | ~435 - 1129 | | |
| | Cu ₂ S / tetragonal | > 1 Kbar | | |
| | Cu _{1.8+x} S / cubic (high digenite) | 83 - 1129 | | |
| | Cu _{1.97} S / orthorhombic (djurleite) | 93 | | |
| | Cu _{1.8} S / cubic (digenite) | 76 - 83 | | |
| | Cu _{1.78} S / monoclinic (roxbyite) | - | | |
| | Cu _{1.75} S / orthorhombic (anilite) | 76 | | |
| | Cu _{1.60} S / cubic (geerite) | - | | |
| | Cu _{1.4} S / hexagonal-R (spionkopite) | - | | |
| | Cu ₉ S ₈ / hexagonal-R (yarrowite) | up to 157 | | |
| | CuS / hexagonal-R (covellite) | up to 507 | | |
| | CuS ₂ / cubic (villamaninite) | - | | |
| | Cu ₃ AsS ₄ (Luzonite) | 275 - 320 | [59, 82] | |
| | Cu ₃ AsS ₄ (Enargite) | 671 | | |
| | Cu ₂₄ As ₁₂ S ₃₁ (-) | 578 | | |
| | Cu ₆ As ₄ S ₉ (Sinnerite) | 489 | | |
| | Cu ₁₂ AsS ₁₃ (Tennantite) | 665 | | |
| | CuAsS (Lautite) | 574 | | |
| Cu ₃ AsS ₃ (near- Tennantite) (-) | 656 | [83] | | |
| Cu _{12 ± x} AsS _{13 ± x} (Tennantite) | 656 | [84] | | |

- (Continued.)

| | | | |
|------------------------------------|--|---|----------------------|
| Ni-As-S | NiAsS (gersdorffite) | above 700 | [72, 85] |
| Cu-Pb-S | Cu ₁₄ Pb ₂ S _{9-x} (0 < x < 0.15) | 486 - 528 | [86, 87, 88] |
| Cu-Sb-S | Sb ₂ S ₃ (stibnite) | 550 | [89] |
| | Cu ₃ SbS ₄ (famatinite) | 627 ± 2 | [69, 90] |
| | CuSbS ₂ (chalcostibnite) | 553 ± 2 | |
| | Cu _{12+x} Sb _{4+y} S ₁₃ | 543 | |
| | Cu ₃ SbS ₃ (skinnerite, low T(mon.)) → Cu ₃ SbS ₃ (skinnerite, high T(orth.)) | 122 ± 3 | |
| | Cu ₃ SbS ₃ (skinnerite) | 607.5 ± 3 | |
| Sb-As-S | AsSbS ₃ (getchellite) As _{0.98} Sb _{1.02} S _{3.00} (getchellite) | 345 | |
| | (As, Sb) ₁₁ S ₁₈ (wakabayashilite) | | |
| | AsSb ₂ S ₂ (pääkkönenite) | 538 | |
| Cu-Zn-S | ZnS (sphalerite, sph) | 1185 (sublimation) 1830 (congruent at 3.7 atm) 1013 - 1130 (sph to wurt inversion based on the amount of S) | [81] |
| | ZnS (wurtzite, wurt) | | |
| | Cu ₃ ZnS ₄ | < 200 ? | |
| Cu-Nb-S | Nb ₁₄ S ₅ | 1500 | [12,35,40,4 1,42] |
| | Nb ₂₁ S ₈ | - | |
| | Nb ₁₀ S ₉ | - | |
| | αNbS | - | |
| | βNbS | - | |
| | Nb ₃ S ₄ | - | |
| | αNbS ₂ | - | |
| | βNbS ₂ | - | |
| | αNbS ₃ | 0 - 630 | |
| | Cu ₃ NbS ₄ | - | |
| Cu _{0.7} NbS ₂ | - | | |
| Cu-Mo-S | MoS ₂ (molybdenite) | 1750 ± 50 | [12] |
| | Mo ₂ S ₃ | ~ 1800 | |
| | ~CuMo ₂ S ₃ | 594- (> 1000) | |
| Mo-Bi-S | Bi ₂ S ₃ (bismuthinite) | 25 - 775 | [91] |

- (Continued.)

| | | | |
|----------------|--|-------------------------|------------------|
| Cu-Bi-S | Cu_9BiS_6 (-) | 400 - 650 | [64, 81] |
| | Cu_3BiS_3 (wittichenite) | 25 - 510 | |
| | CuBiS_2 (cuprobismutite) | 25 - 485 | |
| | $\text{Cu}_3\text{Bi}_3\text{S}_7$ (-) | ~498 | |
| | $\text{Cu}_3\text{Bi}_5\text{S}_9$ | 425 - 590 | |
| | CuBi_3S_5 | 400 - 645 | |
| | $\text{Cu}_{24}\text{Bi}_{26}\text{S}_{51}$ (empletite → cuprobismutite) | $319 \pm 2 - 474 \pm 5$ | [92] |
| Pb-Bi-S | $\text{Pb}_6\text{Bi}_2\text{S}_9$ (heyrovskyite) (> 400 °C composition changes to $\text{Pb}_9\text{Bi}_4\text{S}_{15}$ [65]) | 25 - 829 | [65, 66, 76, 81] |
| | $\text{Pb}_8\text{Bi}_6\text{S}_{17}$ (-) | <400 - 816 | |
| | $\text{Pb}_2\text{Bi}_2\text{S}_5$ (cosalite) | 25 - 425 | |
| | PbBi_2S_4 (galenobismutite) | 25 - 750 | |
| | $\text{Pb}_3\text{Bi}_2\text{S}_6$ (lillianite) | 816 | |
| | PbBi_4S_7 (bonchevite) | 680 - 730 | |
| | $\text{Pb}_5\text{Bi}_4\text{S}_{11}$ (bursaite) | - | |
| | $\text{PbBi}_6\text{S}_{10}$ (ustarasite) | - | |
| Sb-Bi-S | $(\text{Bi}, \text{Sb})_2\text{S}_3$ (horobetsuite) | > 200 | [97, 98] |
| Bi-Se-S | $\text{Bi}_4(\text{S}, \text{Se})_3$ (ikunolite) | - | [100, 101, 102] |
| Bi-Te-S | $\text{Bi}_2\text{Te}_{1.5+x}\text{S}_{1.5-x}$ (δ -tetradymite) | - | [103, 104, 105] |
| | $\text{Bi}_2\text{Te}_{2+x}\text{S}_{1-x}$ (β -tetradymite) | - | |
| | $\text{Bi}_8\text{Te}_7\text{S}_5$ | - | |
| | $\text{Bi}_{18}(\text{TeS}_3)_3$ (joseite-C) | - | |
| | $\text{Bi}_9(\text{Te}_2\text{S}_2)$ | - | |
| | $\text{Bi}_{15}(\text{TeS}_4)$ | - | |
| Pb-Sb-S | $\text{Pb}_3\text{Sb}_2\text{S}_6$ (-) | 610 - 642 | [68] |
| | $\text{Pb}_5\text{Sb}_4\text{S}_{11}$ (boulangerite) | 25 - 638 | |
| | $\text{Pb}_5\text{Sb}_6\text{S}_{14}$ (-) | 425 - 603 | |
| | $\text{Pb}_6\text{Sb}_{10}\text{S}_{21}$ (robinsonite) | 25 - 582 | |
| | PbSb_2S_4 (zinckenite) | 25 - 545 | |

Due to increasing association of impurities in the copper and nickel ore minerals and concentrates, the production of high grade Cu and Ni by the conventional pyrometallurgical processes is compromised. Thus, smelters are in need to modify their operating flow sheets and strategies for processing more complex feed materials economically, while meeting the strict environmental regulations. To make the appropriate modifications, a thorough evaluation of the thermochemistry and thermal stabilities of phases and phase assemblages existing in these complex ore minerals is essential.



ISBN 978-952-60-4531-3
ISBN 978-952-60-4532-0 (pdf)
ISSN-L 1799-4896
ISSN 1799-4896
ISSN 1799-490X (pdf)

Aalto University
School of Chemical Technology
Department of Materials Science and Engineering
www.aalto.fi

**BUSINESS +
ECONOMY**

**ART +
DESIGN +
ARCHITECTURE**

**SCIENCE +
TECHNOLOGY**

CROSSOVER

**DOCTORAL
DISSERTATIONS**